

Flanges and their joints — Circular flanges for pipes, valves, fittings and accessories, PN designated —

Part 1: Steel flanges

The European Standard EN 1092-1:2001 has the status of a
British Standard

ICS 23.040.60

National foreword

This British Standard is the official English language version of EN 1092-1:2001. It supersedes BS 4504-3.1:1989 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PSE/15, Flanges, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users of this publication are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard, having been prepared under the direction of the Engineering Sector Policy and Strategy Committee, was published under the authority of the Standards Policy and Strategy Committee on 08 January 2002

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 70, an inside back cover and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments
13960 Corrigendum No. 1	1 July 2002	Correction of values for neck diameter N_1 in Table 7

© BSI 1 July 2002

ISBN 0 580 38236 2

ICS 23.040.60

English version

Flanges and their joints — Circular flanges for pipes, valves, fittings and accessories, PN designated — Part 1: Steel flanges

Brides et leurs assemblages — Brides circulaires pour tubes, appareils de robinetterie, raccords et accessoires désignées PN — Partie 1: Brides en acier

Flansche und ihre Verbindungen — Runde Flansche für Rohre, Armaturen, Formstücke und Zubehörteile, nach PN bezeichnet — Teil 1: Stahlflansche

This European Standard was approved by CEN on 6 July 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

Page

Foreword	3
Introduction	4
1 Scope	4
2 Normative references	5
3 Terms and definitions	7
3.1 DN	7
3.2 PN7	7
3.3 maximum allowable pressure, <i>PS</i>	7
3.4 maximum allowable temperature, <i>TS</i>	7
4 Designation	7
4.1 General	7
4.2 Standard designation	7
5 General requirements	8
5.1 Flange materials	8
5.2 Repairs	9
5.3 Bolting	9
5.4 Gaskets	9
5.5 Pressure/temperature (p/T) ratings	9
5.6 Dimensions	10
5.7 Flange facings	11
5.8 Spot facing or back facing of flanges	12
5.9 Tolerances	12
5.10 Marking	12
Annex A (normative) Butt weld-end preparation	53
Annex B (informative) Material groups	54
Annex C (informative) Approximate masses of flanges and collars	56
Annex D (informative) Additional materials	64
Annex E (informative) Determination of p/T ratings for flanges using EN materials	65
Annex F (informative) Determination of p/T ratings for flanges using ASTM materials	66
Annex ZA (informative) Essential safety requirements — Clauses of this European Standard addressing essential requirements or other provisions of EU Directives	68
Bibliography	70

Foreword

This document (EN 1090-1:2001) has been prepared by Technical Committee CEN/TC 74, Flanges and their joints, the Secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2002, and conflicting national standards shall be withdrawn at the latest by June 2002.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative annex ZA, which is an integral part of this document.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

EN 1092 consists of the following four parts:

Part 1: Steel flanges;

Part 2: Cast iron flanges;

Part 3: Copper alloy flanges;

Part 4: Aluminium alloy flanges.

This standard includes one normative and eight informative annexes.



Introduction

When Technical Committee CEN/TC 74 commenced its work of producing this European Standard it took as its basis the International Standard ISO 7005-1, Steel flanges.

In taking this decision, CEN/TC 74, agreed that this standard would differ significantly from the ISO standard in respect of the following:

- a) Whereas ISO 7005-1 included in its scope both the original DIN based flanges and also the original ANSI/ASME based flanges, EN 1092-1 contains only the DIN based flanges. CEN/TC 74 has produced a separate series of standards, prEN 1759-1:2000, prEN 1759-3:1994 and prEN 1759-4:1997, dealing with the ANSI/ASME based flanges in their original Class designations.
- b) The opportunity was taken to revise some of the technical requirements applicable to the DIN origin flanges.

Consequently, whilst the mating dimensions, the flange and facing types and designations are compatible with those given in ISO 7005-1, it is important to take account of the following differences which exist in EN 1092-1:

- 1) The p/T ratings of this standard have been reduced in many cases by either limiting the lower temperature ratings which can no longer exceed the PN value, or by increasing the rate at which allowable pressures shall reduce with increase in temperature.
- 2) In addition to the range of PN 2,5 to PN 40 DIN origin flanges contained in the ISO standard, EN 1092-1 also includes PN 63 and PN 100 flanges.
- 3) This standard specifies grades of European steels similar to those specified in ISO 7005-1, but in addition permits the use of those grades of ASTM steels which are specified in the ISO standard for use with the ANSI/ASME based flanges.
- 4) This standard gives an informative annex concerning requirements of EU Directives.

1 Scope

This European Standard for a single series of flanges specifies requirements for circular steel flanges in PN designations PN 2,5 to PN 100 and nominal sizes from DN 10 to DN 4 000.

This standard specifies the flange types and their facings, dimensions, tolerances, threading, bolt sizes, flange jointing face surface finish, marking, materials, pressure/ temperature ratings and approximate flange masses.

This standard does not apply to flanges made from bar stock by turning, or to flanges of types 11, 12 and 13 made from plate material.

2 Normative references

This European Standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 764, *Pressure equipment — Terminology and symbols — Pressure, temperature, volume.*

EN 1333, *Pipework components — Definition and selection of PN.*

EN 1708-1, *Welding — Basic weld joint details in steel — Part 1: Pressurized components.*

EN 10025, *Hot rolled products of non-alloy structural steels — Technical delivery conditions.*

prEN 10028-2:2000, *Flat products made of steels for pressure purposes — Part 2: Non alloy and alloy steels with specified elevated temperature properties.*

prEN 10028-3:2000, *Flat products made of steels for pressure purposes — Part 3: Weldable fine grade steels, normalized.*

prEN 10028-4:2000, *Flat products made of steels for pressure purposes — Part 4: Nickel alloy steels with specified low temperature properties.*

EN 10028-7, *Flat products made of steels for pressure purposes — Part 7: Stainless steels.*

EN 10213-2, *Technical delivery conditions for steel castings for pressure purposes — Part 2: Steel grades for use at room temperature and elevated temperatures.*

EN 10213-3, *Technical delivery conditions for steel castings for pressure purposes — Part 3: Steel grades for use at low temperatures.*

EN 10213-4, *Technical delivery conditions for steel castings for pressure purposes — Part 4: Austenitic and austenitic-ferritic steel grades.*

EN 10222-2, *Steel forgings for pressure purposes — Part 2: Ferritic and martensitic steels with specified elevated temperature properties.*

EN 10222-3, *Steel forgings for pressure purposes — Part 3: Nickel steel with specified low temperature properties.*

EN 10222-4, *Steel forgings for pressure purposes — Part 4: Weldable fine grain steels with high proof strength.*

EN 10222-5, *Steel forgings for pressure purposes — Part 5: Austenitic, martensitic and austenitic-ferritic stainless steels.*

prEN ISO 9692-1:2000, *Welding and allied processes — Recommendation for joint preparation — Part 1: Manual metal-arc welding, gas-shielded metal-arc welding and gas welding of steels (ISO/DIS 9692-1:2000).*

EN ISO 9692-2, *Welding and allied processes — Joint preparation — Part 2: Submerged arc welding of steels (ISO 9692-2:1998).*

EN 1092-1:2001 (E)

EN ISO 6708, *Pipe components — Definition of DN (nominal size) (ISO 6708:1995).*

ISO 7-1, *Pipe threads where pressure-tight joints are made on the threads — Part 1: Dimensions, tolerances and designation.*

ISO 7-2, *Pipe threads where pressure tight joints are made on the threads — Part 2: Verification by means of limit gauges.*

ISO 887, *Plain washers for metric bolts, screws and nuts — General plan.*

ASTM A105/A105M, *Forgings, Carbon Steel, for Piping Components.*

ASTM A182/A 182M, *Forged or Rolled Alloy-Steel Pipe Flanges, Forged Fittings, and Valves and Parts for High-Temperature Service.*

ASTM A203/A203M, *Pressure Vessel Plates, Alloy Steel, Nickel.*

ASTM A204/A204M, *Specification for pressure vessel plates, alloy steel, molybdenum.*

ASTM A216/A216M, *Steel Castings, Carbon Suitable for Fusion Welding for High-Temperature Service.*

ASTM A217/A217M, *Steel Castings, Martensitic Stainless and Alloy, for Pressure-Containing Parts Suitable for High-Temperature Service.*

ASTM A240/A240M, *Heat-Resisting Chromium and Chromium-Nickel Stainless Steel Plate, Sheet, and Strip for Pressure Vessels.*

ASTM A325, *High-Strength Bolts for Structural Steel Joints.*

ASTM A350/A350M, *Forgings, Carbon and Low-Alloy Steel, Requiring Notch Toughness Testing for Piping Components.*

ASTM A351/A351M, *Castings, Austenitic, Austenitic-Ferritic (Duplex) for Pressure-Containing Parts.*

ASTM A352/A352M, *Steel Castings, Ferritic and Martensitic, for Pressure-Containing Parts Suitable for Low-Temperature Service.*

ASTM A387/A387M, *Pressure Vessel Plates, Alloy Steel, Chromium-Molybdenum.*

ASTM A515/A515M, *Pressure Vessel Plates, Carbon Steel, for Intermediate and Higher-Temperature Service.*

ASTM A516/A516M, *Pressure Vessel Plates, Carbon Steel, for Moderate and Lower-Temperature Service.*

ASTM A537/A537M, *Pressure Vessel Plates, Heat-Treated, Carbon-Manganese-Silicon Steel.*

3 Terms and definitions

For the purposes of this standard the following terms and definitions apply.

3.1

DN

see EN ISO 6708

3.2

PN

see EN 1333

3.3

maximum allowable pressure, *PS*

means the maximum pressure for which the equipment is designed, as specified by the equipment manufacturer

3.4

maximum allowable temperature, *TS*

means the maximum temperature for which the equipment is designed, as specified by the equipment manufacturer

4 Designation

4.1 General

Table 1 specifies the flange types and ancillary components.

Figures 1 and 2 show flange types and ancillary components with the relevant flange type numbers. Flanges shall be denoted with “flange type” and the “flange number”. Ancillary components shall be denoted with ancillary component type and the type number.

Figure 3 shows flange facing types, which may be used with the flanges or components shown in Figures 1 and 2. Flange facings shall be denoted with “type” and the relevant symbol.

The range of DN, applicable to each flange type and to each PN, shall be as given in Table 3.

4.2 Standard designation

Flanges and ancillary components in accordance with this standard shall be designated with the following:

- a) Designation, e.g. flange, lapped end or collar.
- b) Number of this standard, EN 1092-1.
- c) Number of flange type in accordance with Figures 1 and 2.
- d) Type of flange facing in accordance with Figure 3.
- e) DN (nominal size).
- f) PN designation.
- g) Neck thickness *S* (only for types 11 and 34).

EN 1092-1:2001 (E)

- h) For type 13 flanges type of thread (R_p or R_c).
- i) Bore diameter (for sizes greater than DN 600):
 - B_1 (only for types 01, 12 and 32);
 - B_2 (only for type 02);
 - B_3 (only for type 04).
- j) Either the symbol or the number or the grade of the material (see Tables 5a and 5b).
- k) Any heat treatment required.
- l) Material certificate, if required (see 5.1).

EXAMPLE 1

Designation of a flange type 01 with facing type A and nominal size DN 800, of PN 6 with bore diameter $B_1 = 818$ mm, made of material with the symbol S235JR:

Flange EN 1092-1/01 A/DN 800/PN 6/818/S235JR.

EXAMPLE 2

Designation of an ancillary component type 32 with facing type A of nominal size DN 400, PN 10 and made of material with the symbol S235JR:

Collar EN 1092-1/32 A/DN 400/PN 10/S235JR.

EXAMPLE 3

Designation of a flange type 02 with facing type A of nominal size DN 400, PN 10 and made of material with the number 1.0038:

Flange EN 1092-1/02 A/DN 400/PN 10/1.0038.

EXAMPLE 4

Designation of a flange type 11 with facing type B2 of nominal size DN 200, PN 100 and with neck thickness, $S = 10$ mm, made of material with the symbol 13CrMo4-5:

Flange EN 1092-1/11 B2/DN 200/PN 100/10/13CrMo4-5.

5 General requirements

5.1 Flange materials

Flanges shall be manufactured from materials given in Tables 5a and 5b (see also annex D). For type 11, 12 and 13 flanges, the manufacture shall be from forgings. For type 21 flanges the manufacture shall be from forgings or steel castings.

The flange manufacturer shall provide documentation to ensure traceability of material. An equipment manufacturer may require a certificate in accordance with EN 10204 which is suitable for the category of equipment to which the flange is fitted.

NOTE 1 The materials given in Tables 5a and 5b (see also annex D) are tabulated in groups having the same p/T ratings as given in Tables 15, 16, 17, 18, 19 and 20 (see annex B).

NOTE 2 The materials of ancillary components are not within the scope of this standard.

5.2 Repairs

Where not otherwise prohibited by the applicable material standard, repairs by welding are permitted when there is a proven method. All welding shall be carried out in accordance with a written procedure.

NOTE For approval of welding procedures, see EN 288-1. For approval of welders, see EN 287-1.

5.3 Bolting

Flanges shall be suitable for use with the number and size of bolting as specified in Tables 6 to 13. The bolting shall be chosen by the equipment manufacturer according to the pressure, temperature, flange material and gasket so that the flanged joint remains tight under the expected operating conditions. For selection of bolting, see EN 1515-1, for combination of the materials of flanges and bolting see prEN 1515-2:1994, for information.

5.4 Gaskets

The various gasket types, dimensions, design characteristics and materials used are not within the scope of this standard. Dimensions of gaskets are given in EN 1514-1 to EN 1514-4.

5.5 Pressure/temperature (p/T) ratings

The p/T ratings of flanges are given in Tables 15, 16, 17, 18, 19 and 20.

The p/T ratings indicate the relationship between the maximum allowable pressure PS and the maximum allowable temperature.

The p/T ratings shall apply only for flange types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600. The p/T ratings of all other flanges shall be calculated or subject to special experience.

NOTE 1 The rules for the determination of p/T ratings of the above tables are given in annexes E and F.

NOTE 2 For the material groups 10E0 to 16E0 (austenitic steels), Tables 17 and 18 should be used as follows:

- Table 17 should be chosen for application in cases where the flange deformation has to be strictly limited.
- Table 18 should be chosen in all cases where a small amount of plastic deformation of the flanges can be considered acceptable.

NOTE 3 Linear interpolation is permitted for intermediate temperatures.

For interpolation between (-10 °C to 50 °C) and 100 °C, 20 °C shall be used.

NOTE 4 The relevant pressures and temperatures are those of the fluid in the pipework system.

5.6 Dimensions

5.6.1 Flanges

The dimensions of flanges shall be as given in Tables 6 to 13 according to the PN designation. Dimension G_{\max} may be varied from the given value (see NOTE 1) which is a maximum limit. The neck thickness S is a minimum value selected according to pipe thicknesses given in ISO 4200 (see NOTE 2).

NOTE 1 The centre portion of the face of a flange type 05 need not be machined provided that the diameter of the unmachined portion does not exceed the recommended diameter for G_{\max} given in Tables 6 to 13.

NOTE 2 When requested by the pressure equipment manufacturer, neck thicknesses, other than those given in the relevant tables, may be supplied by agreement with the flange manufacturer.

NOTE 3 A summary of the various types of flanges specified is given in Table 3 showing the nominal sizes applicable to each type and to each PN.

NOTE 4 Diameters N_1 , N_2 and N_3 of flange types 11, 12, 13, 21 and 34 are the theoretical maximum values permitting the use of ring spanners or the application of normal series plain washers without any additional machining, e.g. spot facing (see 5.8).

NOTE 5 The bore diameters of flanges type 21 are not specified in this standard, the effective bore diameters are usually given in the relevant component standard(s).

NOTE 6 Approximate masses of flanges are given in annex C.

NOTE 7 The flange thicknesses for flanges type 05, 11, 12, 13, 21 and PN 6, PN 10, PN 16, PN 25 have an unusual step at DN 600/DN 700. This is based on a change at some flange thicknesses up to and including DN 600 to meet the pressure/temperature ratings (limited to DN 600). The flange thicknesses for flanges DN 700 and above are the same as they are given in the documents of origin (DIN, BS NFE, IBN, etc.). They will be updated in future based on the flange calculation method as far as the corresponding work items of CEN/TC 74/WG 10 gives sufficient results.

NOTE 8 For flanges type 21 dimensions A , N_3 and R_1 are nominal values and are included for guidance only.

5.6.2 Hubs

The hubs of flange types 12 and 13 shall be either:

- a) parallel; or
- b) taper with an angle not exceeding 7° on the outside surface for forging or casting purposes.

Details of the weld-end preparation for flanges type 11 and ancillary components type 33 shall be as given in annex A.

5.6.3 Threaded flanges

5.6.3.1 The threads of flanges type 13 shall be parallel (symbol R_p) or tapered (symbol R_c) in accordance with ISO 7-1. Gauging shall be in accordance with ISO 7-2.

NOTE Parallel threads will be supplied unless otherwise requested by the equipment manufacturer.

5.6.3.2 The thread shall be concentric with the axis of the flange and misalignments shall not exceed 5 mm per metre.

Flanges type 13 shall be manufactured without a parallel counterbore, but to protect the thread they shall be chamfered to the major diameter of the thread at the hubbed side of the flange at an angle between 30° and 50° to the axis of the thread. The chamfer shall be concentric with the thread and shall be included in the measurement of the thread length provided that the chamfer does not exceed one pitch in length.

5.6.4 Bolt holes

Bolt holes shall be equally spaced on the pitch circle diameter. In the case of flanges type 21 they shall be positioned such that they are symmetrical to the principal axes and such that no holes fall on these axes, i.e. positioned "off-centre", see Figures 5 to 12.

5.6.5 Lapped joints

The dimensions of lapped joints to be used with flanges, type 02 and type 04, are specified in Tables 7 to 11.

For ancillary component type 33, the thickness of the lapped end at the facing shall be not less than the specified wall thickness of the pipe used.

5.7 Flange facings

5.7.1 Types of facings

The types of flange facings shall be as given in Figure 3 and their dimensions shall be as given in Figure 4 and Table 4.

For facings types B, D, F and G, the transition from the edge of the raised face to the flange shall be:

- a) radius; or
- b) chamfer;

at the choice of the flange manufacturer.

5.7.2 Jointing face finish

5.7.2.1 All flange jointing faces shall be machine finished and shall have a surface finish in accordance with the values given in Table 2 when compared with reference specimens by visual or tactile means.

NOTE It is not intended that instrument measurements be taken on the faces themselves; the R_a and R_z values as defined in EN ISO 4287 relate to the reference specimens.

5.7.2.2 For flanges with facing types A, B1, E and F, turning shall be carried out with a round nosed tool in accordance with Table 2.

5.7.2.3 Flanges \leq PN 40 shall have type B1 facings and flanges \geq PN 63 shall have type B2 facings, unless otherwise agreed in the order.

5.8 Spot facing or back facing of flanges

Any spot facing or back facing shall not reduce the flange thickness to less than the flange thickness specified. When spot facing is used, the diameter shall be large enough to accommodate the outside diameter of the equivalent normal series of washers in accordance with ISO 887 for the bolt size being fitted. The bearing surfaces for the bolting shall be parallel to the flange face within the limits given in Table 14. When a flange is back faced a minimum fillet radius R_2 (see Figure 13) in accordance with Table 21 shall be maintained.

5.9 Tolerances

Tolerances on dimensions of flanges shall be as given in Table 14.

5.10 Marking

5.10.1 General marking requirements


All flanges, other than type 21 flanges, shall be marked as follows:

- a) Flange manufacturer's name or trade mark, e.g. XXX.
- b) Number of this standard, i.e. EN 1092-1.
- c) Flange type number, e.g. 11.
- d) DN, e.g. DN 150.
- e) PN designation, e.g. PN 40.
- f) Neck thickness (S), if not to this standard.
- g) For EN materials: either the symbol or the number or the grade of the material, e.g. S235JR.
- h) For ASTM materials: the material grade, preceded by the specification number where necessary, e.g. WC 4.
- i) Cast number of melt identification or suitable control number traceable to the cast number, e.g. 12345, when test certification is required.


EXAMPLE XXX/EN 1092-1/11/DN 150/PN 40/S235JR/12345.

If a flange is too small to enable all the markings required then the minimum marking required shall be:


- a) Flange manufacturer's name or trade mark.
- b) Letters "EN".
- e) PN designation, e.g. PN 40.
- g) Either the symbol or the number or the grade of the material.
- h) Cast number or melt identification or suitable control number.




Type 01
Plate flange for welding

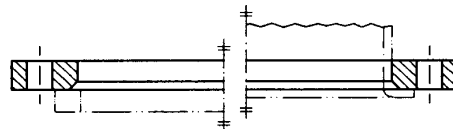


Type 02
Loose plate flange with weld-on collar (see type 32) or lapped pipe end (see type 33)




Type 04
Loose plate flange with weld-neck collar (see type 34)




Type 05
Blank flange




Type 11
Weld-neck flange



Type 12
Hubbed slip-on flange for welding



Type 13
Hubbed threaded flange

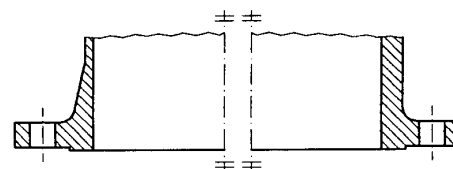

Type 21
Integral flange

NOTE These sketches are diagrammatic only, in particular no detail is shown for the mating surfaces (see Figure 3).

Figure 1 — Flange types


Table 1 — Types of steel flanges and ancillary components

Type No.	Description
01	Plate flange for welding
02	Loose plate flange with weld-on plate collar or for lapped pipe end
04	Loose plate flange with weld-neck collar
05	Blank flange
11	Weld-neck flange
12	Hubbed slip-on flange for welding
13	Hubbed threaded flange
21 ^a	Integral flange
32 ^b	Weld-on plate collar
33 ^b	Lapped pipe end
34 ^b	Weld-neck collar

^a Flange type 21 is an integral part of some other equipment or component.


^b Ancillary components type numbers 32 and 33 are for use with type 02 flanges and type number 34 for use with type 04 flanges.

NOTE Type numbers have been made non-consecutive to permit possible future additions.

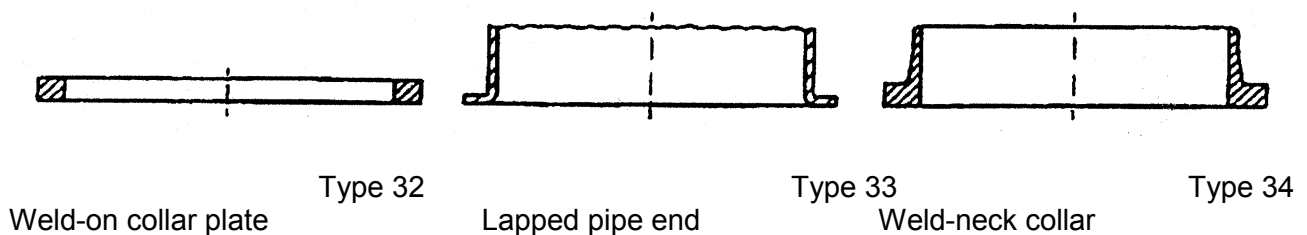

NOTE These sketches are diagrammatic only.

Figure 2 — Ancillary components types 32 to 34

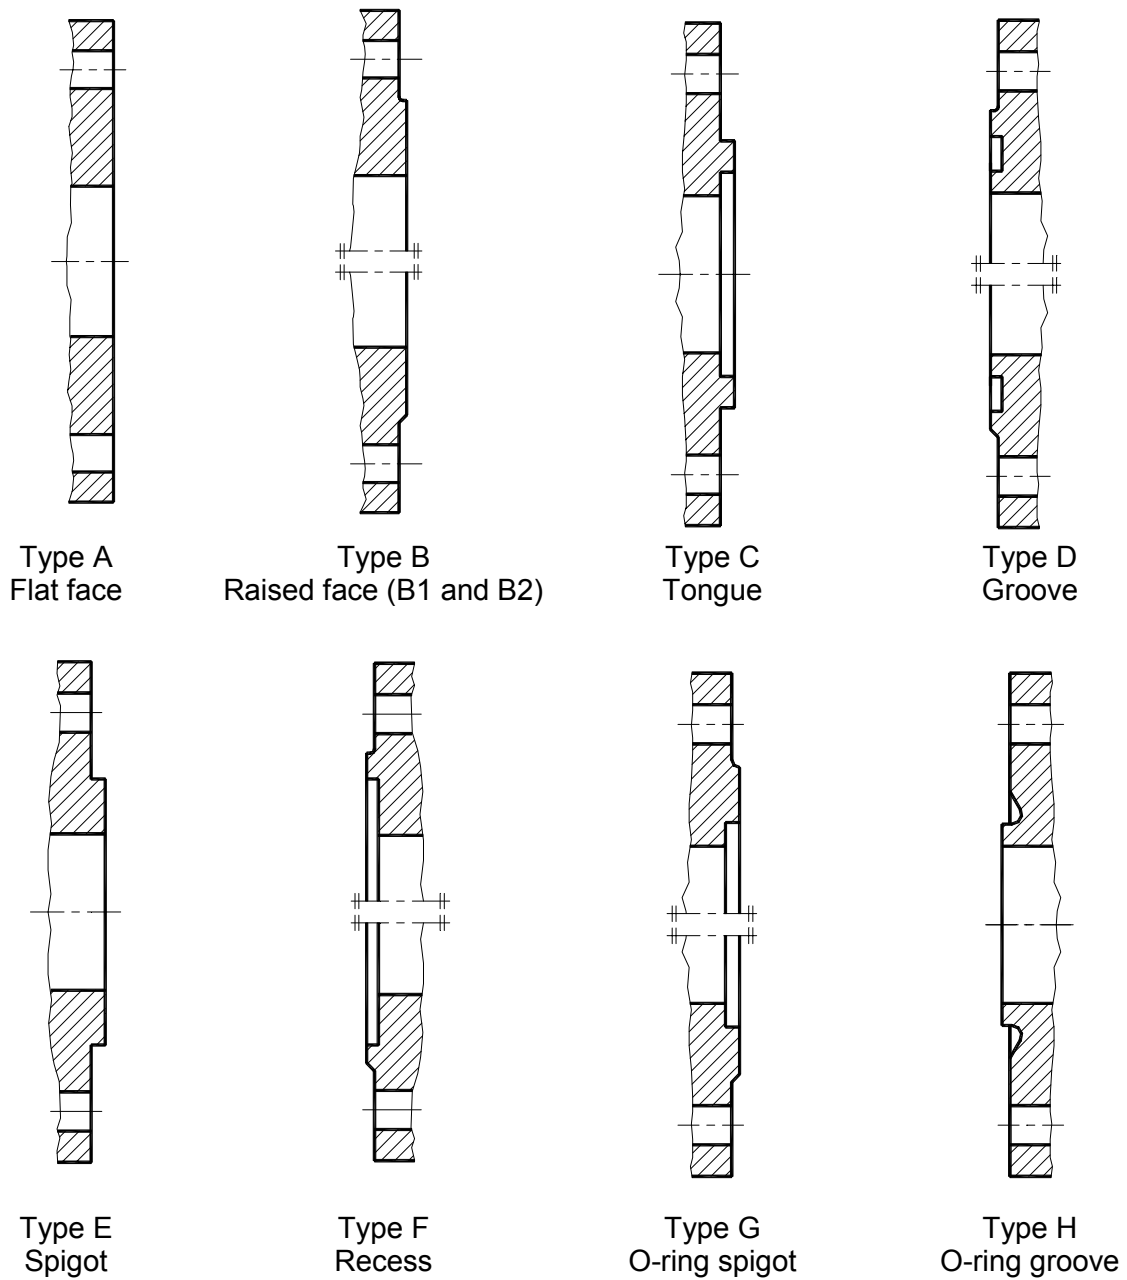

NOTE 1 The transition from the edge of the raised face to the flange face may be by radius or chamfer for types B, D, F and G only (see 5.7.1).

NOTE 2 B1 and B2 are raised face (type B) for different applications (see 5.7.2.2, 5.7.2.3 and Table 2).

NOTE 3 For the dimensions of flange facings, see Figure 4 and Table 4.

Figure 3 — Flange facing types

Table 2 — Surface finish for jointing faces

Facing types	Method of machining	Radius of tool nose mm min.	R_a^a		R_z^a	
			μm		μm	
			min.	max.	min.	max.
A, B1 ^b , E, F	Turning ^c	1,0	3,2	12,5	12,5	50
B2 ^b , C, D, G, H	Turning ^c	—	0,8	3,2	3,2	12,5

^a R_a and R_z are defined in EN ISO 4287.


^b Types B1 and B2 are raised face (type B) flanges with different specified surface roughness values for the following applications:

B1 for PN 2,5 up to PN 40;


B2 for PN 63 and PN 100.

^c The term “turning” includes any method of machine operation producing either serrated concentric or serrated spiral grooves.


NOTE For certain applications, e.g. low temperature gases, it may be necessary to stipulate closer control to the surface finish.

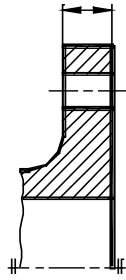


Type A: Flat face

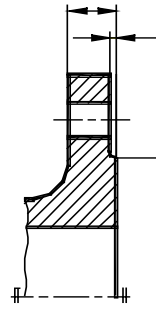


Type B: Raised face (B1 and B2)

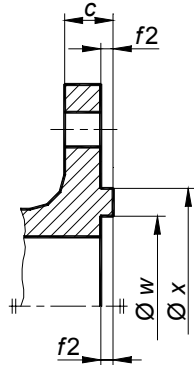


Type C: Tongue

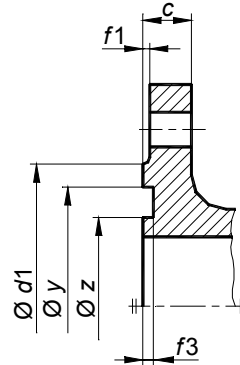


Type D: Groove

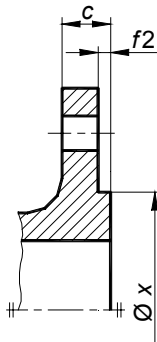


Type E: Spigot

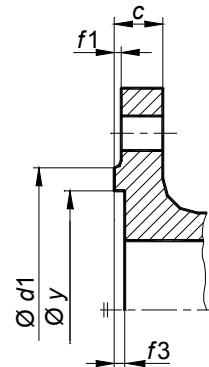

Type F: Recess

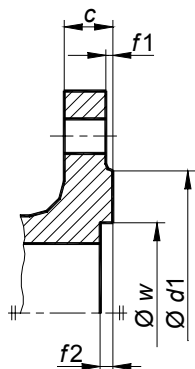

Type G: O-ring spigot

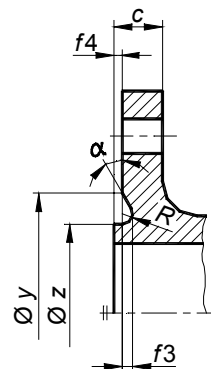

Type H: O-ring groove

NOTE 1 Dimension *C* includes the raised face thickness.

NOTE 2 Cross section diameter of the O-ring is $2 \times R$.

Figure 4 — Flange facing (dimensions see Table 4)

EN 1092-1:2001 (E)

Table 4 — Flange facing dimensions

DN	d_1								f_1	f_2	f_3	f_4	w	x	y	z	$\alpha \approx$	R		
	PN 2,5	PN 6	PN 10	PN 16	PN 25	PN 40	PN 63	PN 100												
	mm	mm	mm	mm	mm	mm	mm	mm												
10	Use PN 6 dimensions	35	Use PN 100 dimensions					40	2	4,5	4,0	2,0	24	34	35	23	—	2,5		
15		40	45	29	39	40	28	—												
20		50	58	36	50	51	35	—												
25		60	68	43	57	58	42	41°												
32		70	78	51	65	66	50													
40		80	88	61	75	76	60													
50		90	102	73	87	88	72													
65		110	122	95	109	110	94													
80		128	138	106	120	121	105													
100		148	158	162	162	162	162	129					149	150	128	32°	3			
125		178	188	188	188	188	188	155					175	176	154					
150		202	212	218	218	218	218	183					203	204	182					
200		258	268	278	285	285	285	239					259	260	238					
250		312	320	335	345	345	345	292					312	313	291					
300		365	370	395	410	410	410	343					363	364	342					
350		Use PN 6 dimensions	415	430	438	450	465	465					465	395	421	422	394		27°	3,5
400			465	482	490	505	535	535					535	447	473	474	446			
450			520	532	550	555	560	560					560	497	523	524	496			
500	570		585	610	615	615	615	615	549	575	576	548								
600	670		685	725	720	735	735	—	649	675	676	648								
700	775		800	795	820	—	840	—	751	777	778	750								
800	880		905	900	930	—	960	—	856	882	883	855								
900	980		1 005	1 000	1 030	—	1 070	—	961	987	988	960								
1 000	1 080		1 110	1 115	1 140	—	1 180	—	1 062	1 092	1 094	1 060								
1 200	1 280		1 295	1 330	1 350	—	1 380	—	1 262	1 292	1 294	1 260								
1 400	1 480		1 510	1 535	1 560	—	—	—	1 462	1 492	1 494	1 460								
1 600	1 690		1 710	1 760	1 780	—	—	—	1 662	1 692	1 694	1 660								
1 800	1 890		1 920	1 960	1 985	—	—	—	1 862	1 892	1 894	1 860								
2 000	2 090		2 125	2 170	2 150	2 210	—	—	2 062	2 092	2 094	2 060								
2 200	2 295		2 335	2 370	—	—	—	—	—	—	—	—	—							
2 400	2 495		2 545	2 570	—	—	—	—	—	—	—	—	—							
2 600	2 695		2 750	2 780	—	—	—	—	—	—	—	—	—							
2 800	2 910		2 960	3 000	—	—	—	—	—	—	—	—	—							
3 000	3 110	3 160	3 210	—	—	—	—	—	—	—	—	—								
3 200	3 310	3 370	—	—	—	—	—	—	—	—	—	—								
3 400	3 510	3 580	—	—	—	—	—	—	—	—	—	—								
3 600	3 720	3 790	—	—	—	—	—	—	—	—	—	—								
3 800	3 920	—	—	—	—	—	—	—	—	—	—	—								
4 000	4 120	—	—	—	—	—	—	—	—	—	—	—								

Table 5a — Materials — EN

Group	Forgings			Castings			Hot rolled products		
	Symbol	Standard	Material number	Symbol	Standard	Material number	Symbol	Standard	Material number
1E0	S235JR	EN 10025	1.0037	—	—	—	S235JR	EN 10025	1.0037
1E1	S235JRG2	EN 10025	1.0038	—	—	—	S235JRG2	EN 10025	1.0038
2E0	—	—	—	GP240GR	EN 10213-2	1.0621	—	—	—
3E0	P245GH	EN 10222-2	1.0352	GP240GH	EN 10213-2	1.0619	P265GH	EN 10028-2	1.0425
3E1	P280GH	EN 10222-2	1.0426	—	—	—	P295GH	EN 10028-2	1.0481
4E0	17Mo3	EN 10222-2	1.5445	G20Mo5	EN 10213-2	1.5419	16Mo3	EN 10028-2	1.5415
5E0	14CrMo4-5	EN 10222-2	1.7335	G17CrMo5-5	EN 10213-2	1.7357	13CrMo4-5	EN 10028-2	1.7335
6E0	11CrMo9-10	EN 10222-2	1.7383	G17CrMo9-10	EN 10213-2	1.7379	11CrMo9-10	EN 10028-2	1.7383
6E1	X16CrMo5-1+NT	EN 10222-2	1.7366	GX15CrMo5	EN 10213-2	1.7365	—	—	—
7E0	13MnNi6-3	EN 10222-3	1.6217	G17Mn5	EN 10213-3	1.1131	P275NL1	EN 10028-3	1.0488
—	—	—	—	G20Mn5	EN 10213-3	1.6220	P275NL2	EN 10028-3	1.1104
7E1	—	—	—	—	—	—	11MnNi5-3	EN 10028-4	1.6212
—	—	—	—	—	—	—	P355NL1	EN 10028-3	1.0566
—	—	—	—	—	—	—	P355NL2	EN 10028-3	1.1106
—	15NiMn6	EN 10222-3	1.6228	—	—	—	15NiMn6	EN 10028-4	1.6228
—	12Ni14	EN 10222-3	1.5637	G9Ni14	EN 10213-3	1.5638	12Ni14	EN 10028-4	1.5637
—	12Ni19	EN 10222-3	1.5680	—	—	—	12Ni19	EN 10028-4	1.5680
7E2	X8Ni9	EN 10222-3	1.5662	—	—	—	X8Ni9	EN 10028-4	1.5662
7E3	13MnNi6-3	EN 10222-3	1.6217	—	—	—	11MnNi5-3	EN 10028-4	1.6212
—	12Ni14	EN 10222-3	1.5637	—	—	—	12Ni14	EN 10028-4	1.5637
—	—	EN 10222-3	1.5680	—	—	—	12Ni19	EN 10028-4	1.5680
—	X8Ni9	EN 10222-3	1.5662	—	—	—	X8Ni9	EN 10028-4	1.5662
8E0	—	—	—	—	—	—	P275N	EN 10028-3	1.0486
8E1	—	—	—	—	—	—	P355N	EN 10028-3	1.0562
8E2	P285NH	EN 10224-4	1.0487	—	—	—	P275NH	EN 10028-3	1.0487
8E3	P355NH	EN 10224-4	1.0565	—	—	—	P355NH	EN 10028-3	1.0565
9E0	X20CrMoV11-1	EN 10222-2	1.4922	GX23CrMoV12-1	EN 10213-2	1.4931	—	—	—
10E0	X2CrNi18-9	EN 10222-5	1.4307	GX2CrNi19-11	EN 10213-4	1.4309	X2CrNi18-9	EN 10028-7	1.4306
10E1	X2CrNi18-10	EN 10222-5	1.4311	—	—	—	X2CrNi18-10	EN 10028-7	1.4311
11E0	X5CrNi18-10	EN 10222-5	1.4301	GX5CrNi19-10	EN 10213-4	1.4308	X5CrNi18-10	EN 10028-7	1.4301
12E0	X6CrNiTi18-10	EN 10222-5	1.4541	—	—	—	X6CrNiTi18-10	EN 10028-7	1.4541
—	—	—	—	GX5CrNiNb19-11	EN 10213-4	1.4552	X6CrNiNb18-10	EN 10028-7	1.4550
13E0	X2CrNiMo17-12-2	EN 10222-5	1.4404	GX2CrNiMo19-11-2	EN 10213-4	1.4409	X2CrNiMo17-12-2	EN 10028-7	1.4404
13E1	X2CrNiMoN17-11-2	EN 10222-5	1.4406	—	—	—	—	—	—
14E0	X5CrNiMo17-12-2	EN 10222-5	1.4401	GX5CrNiMo19-11-2	EN 10213-4	1.4408	X5CrNiMo17-12-2	EN 10028-7	1.4401
15E0	X6CrNiMoTi17-12-2	EN 10222-5	1.4571	—	—	—	X6CrNiMoTi17-12-2	EN 10028-7	1.4571
—	—	—	—	GX5CrNiMoNb19-11-2	EN 10213-4	1.4581	X6CrNiMoNb17-12-2	EN 10028-7	1.4580
16E0	—	—	—	GX2CrNiMoCuN25-6-3-3	EN 10213-4	1.4517	—	—	—
—	—	—	—	GX2CrNiMoN26-7-4	EN 10213-4	1.4469	—	—	—

Table 5b — Materials — ASTM

Material group	Specification and grade					
	Casting		Forging		Plate	
	Standard	Grade	Standard	Grade	Standard	Grade
1C1	ASTM A216 ^{a,b}	WCB	ASTM A105 ^{a,b} ASTM A350	— LF2 ^c	ASTM 515 ASTM A516 ASTM A537	70 ^{a,b} 70 ^{a,d} CL1 ^c
1C2	ASTM A216 ASTM A352	WCC ^{a,b} LC2 ^c , LC3 ^c , LCC ^c	ASTM A350	LF3 ^c	ASTM A203	B ^{a,b} , E ^{a,b}
1C3	ASTM A352 ^a	LCB	—	—	ASTM A203 ASTM A515 ASTM A516	A ^{a,b} , D ^{a,b} 65 ^{a,b} 65 ^{a,d}
1C4	—	—	ASTM A350 ^c	LF1	ASTM A515 ASTM A516	60 ^{a,b} 60 ^{a,d}
1C5	ASTM A217 ^{b,e} ASTM A325 ^c	WC1 LC1	ASTM A182 ^{b,e}	F1	ASTM A204	A ^{b,e} , B ^{b,e}
1C7	ASTM A217	WC4 ^b , WC5 ^f	ASTM A182 ^b	F2	ASTM A204 ^d	C
1C9	ASTM A217 ^g	WC6	ASTM A182	F11 ^h , F12 ^h	ASTM A387 ^h	11CL2
1C10	ASTM A217 ^g	WC9	ASTM A182 ^g	F22	ASTM A387 ^h	22CL2
1C13	ASTM A217	C5	ASTM A182	F5, F5A	—	—
1C14	ASTM A217	C12	ASTM A182	F9	—	—
2C1	ASTM A351	CF8, CF3 ⁱ	ASTM A182	F304, F304H	ASTM A240	304, 304H ⁱ
2C2	ASTM A351	CF8M, CF3M ^d	ASTM A182	F316, F316H	ASTM A240	316, 317, 316H ^d
2C3	—	—	ASTM A182	F304L ⁱ , F316L ^d	ASTM A240	304L ⁱ ; 316L ^d
2C4	—	—	ASTM A182	F321 ^b , F321H	ASTM A240	321 ^b , 321H
2C5	—	—	ASTM A182	F347 ^b , F347H, F348 ^b , F348H	ASTM A240	347 ^b , 347H, 348 ^b , 348H
2C6	ASTM A351	CH8, CH20	—	—	ASTM A240	309S
2C7	ASTM A351	CK20	ASTM A182 ^j	F310	ASTM A240 ^j	310S

^a Permissible but not recommended for use above 425 °C.

^b Not to be used over 540 °C.

^c Not to be used over 345 °C.

^d Not to be used over 455 °C.

^e Permissible but not recommended for prolonged use above about 455 °C.


^f Not to be used over 565 °C.

^g Not to be used over 590 °C.

^h Permissible but not recommended for prolonged use above about 590 °C.


ⁱ Not to be used over 425 °C.

^j For service temperature 565 °C and above, should be used only when assurance is provided that grain size is not greater than ASTM No 6.

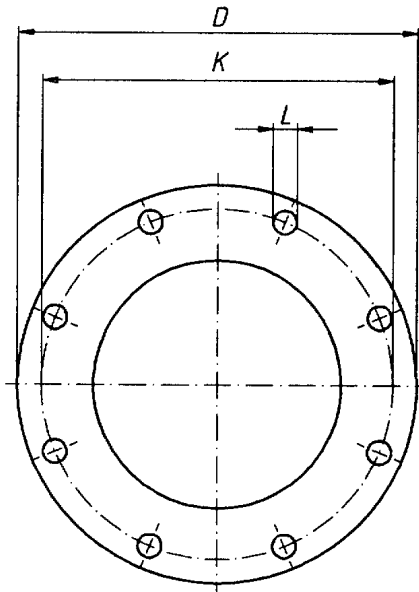


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.


Refer to the column "Bolting Number" in Table 6 for actual number.

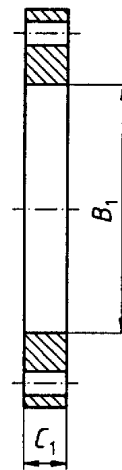

Type 01

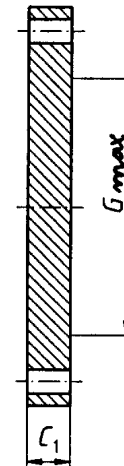

Type 05

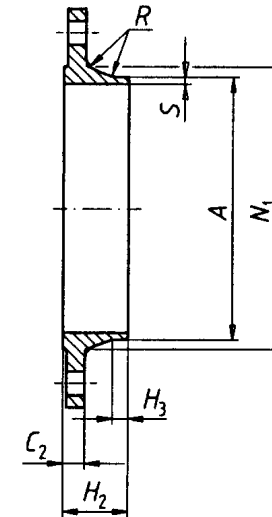

Type 11

NOTE 1 Dimension N_1 is measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimension G_{max} refer to NOTE 1 of 5.6.1.



Figure 5 — Dimensions of PN 2,5 flanges

EN 1092-1:2001 (E)

Table 6 — Dimensions of PN 2,5 flanges


Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameter <i>B₁</i>	Flange thickness		Diameter of shoulder <i>G_{max}</i>	Lengths		Neck diameter <i>N₁</i>	Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting				<i>C₁</i>	<i>C₂</i>		<i>H₂</i>	<i>H₃</i>			
				Number	Size										
	Flange type							11	01		01 05	11			
10 to 1 000	Use PN 6 rating (dimensions for these sizes are identical)														
1 200	1 375	1 320	30	32	M27	1 219			26	1 160	70	16	1 245	16	7
1 400	1 575	1 520	30	36	M27	1 422			26	1 346	70	16	1 445	16	7
1 600	1 790	1 730	30	40	M27	1 626			26	1 546	80	20	1 645	16	8
1 800	1 990	1 930	30	44	M27	1 829			26	1 746	80	20	1 845	16	9
2 000	2 190	2 130	30	48	M27	2 032			26	1 950	80	22	2 045	16	10
2 200	2 405	2 340	33	52	M30	2 235			28	—	90	25	2 248	18	10
2 400	2 605	2 540	33	56	M30	2 438	To be specified by the purchaser	To be specified by the purchaser	28	—	90	25	2 448	18	10
2 600	2 805	2 740	33	60	M30	2 620			28	—	90	25	2 648	18	10
2 800	3 030	2 960	36	64	M33	2 820			30	—	90	25	2 848	18	10
3 000	3 230	3 160	36	68	M33	3 020			30	—	90	25	3 050	18	10
3 200	3 430	3 360	36	72	M33	3 220			30	—	90	25	3 250	20	10
3 400	3 630	3 560	36	76	M33	3 420			32	—	95	28	3 450	20	10
3 600	3 840	3 770	36	80	M33	3 620			32	—	100	28	3 652	20	10
3 800	4 045	3 970	39	80	M36	3 820			34	—	100	28	3 852	20	10
4 000	4 245	4 170	39	84	M36	4 020			34	—	100	28	4 052	20	10

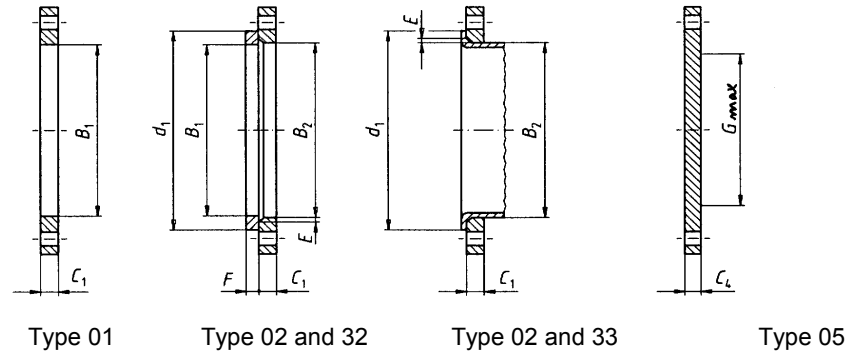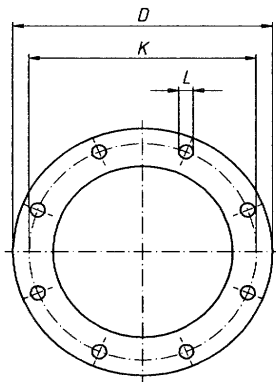

This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.

Refer to the column "Bolting Number" in Table 7 for the actual number.

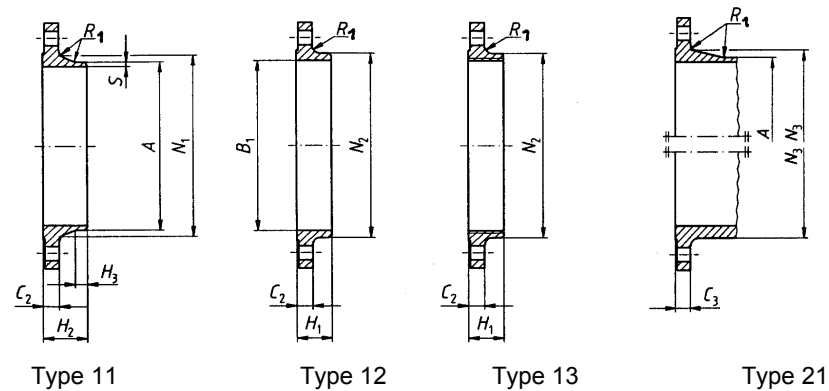

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimension d_1 , see Table 4.

NOTE 3 For dimensions G_{max} refer to NOTE 1 of 5.6.1.

NOTE 4 Type 33; lapped pipe end without determination of thickness.

Figure 6 — Dimensions of PN 6 flanges

EN 1092-1:2001 (E)

Table 7 — Dimensions of PN 6 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters		Flange thickness			Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulder <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>C₁^a</i>	<i>C₂</i>	<i>C₄</i>				<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size																	
	Flange type																					
01, 02, 05, 11, 12, 13, 21						11 21 ^b	01 12 32	02	01 02	11 12 13 21	05	02	32	05	12 13	11	11	11	12 13	21	11 12 13 21	11
10	75	50	11	4	M10	17,2	18,0	21	12	12	12	3	10	—	20	28	6	26	25	20	4	1,8
15	80	55	11	4	M10	21,3	22,0	25	12	12	12	3	10	—	20	30	6	30	30	26	4	2,0
20	90	65	11	4	M10	26,9	27,5	31	14	14	14	4	10	—	24	32	6	38	40	34	4	2,3
25	100	75	11	4	M10	33,7	34,5	38	14	14	14	4	10	—	24	35	6	42	50	44	4	2,6
32	120	90	14	4	M12	42,4	43,5	46	16	14	14	5	10	—	26	35	6	55	60	54	6	2,6
40	130	100	14	4	M12	48,3	49,5	53	16	14	14	5	10	—	26	38	7	62	70	64	6	2,6
50	140	110	14	4	M12	60,3	61,5	65	16	14	14	5	12	—	28	38	8	74	80	74	6	2,9
65	160	130	14	4	M12	76,1	77,5	81	16	14	14	6	12	55	32	38	9	88	100	94	6	2,9
80	190	150	18	4	M16	88,9	90,5	94	18	16	16	6	12	70	34	42	10	102	110	110	8	3,2
100	210	170	18	4	M16	114,3	116,0	120	18	16	16	6	14	90	40	45	10	130	130	130	8	3,6
125	240	200	18	8	M16	139,7	141,5	145	20	18	18	6	14	115	44	48	10	155	160	160	8	4,0
150	265	225	18	8	M16	168,3	170,5	174	20	18	18	6	14	140	44	48	12	184	185	182	10	4,5
200	320	280	18	8	M16	219,1	221,5	226	22	20	20	6	16	190	44	55	15	236	240	238	10	6,3
250	375	335	18	12	M16	273,0	276,5	281	24	22	22	8	18	235	44	60	15	290	295	284	12	6,3
300	440	395	22	12	M20	323,9	327,5	333	24	22	22	8	18	285	44	62	15	342	355	342	12	7,1
350	490	445	22	12	M20	355,6	359,5	365	26	22	22	8	18	330	—	62	15	385	—	392	12	7,1
400	540	495	22	16	M20	406,4	411,0	416	28	22	22	8	20	380	—	65	15	438	—	442	12	7,1
450	595	550	22	16	M20	457,0	462,0	467	30	22	24	8	20	425	—	65	15	492	—	494	12	7,1


Table 7 (continued)

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters		Flange thickness			Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulder <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>C₁^a</i>	<i>C₂</i>	<i>C₄</i>				<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size																	
Flange type																						
01, 02, 05, 11, 12, 13, 21						11 21 ^b	01 12 32	02	01 02	11 12 13 21	05	02	32	05	12 13	11	11	11	11 12 13 21	11		
500	645	600	22	20	M20	508,0	513,5	519	30	24	24	8	22	475	—	68	15	538	—	544	12	7,1
600	755	705	26	20	M24	610,0	616,5	622	32	30	30	8	22	575	—	70	16	640	—	642	12	7,1
700	860	810	26	24	M24	711,0	—	—	—	24	40	—	—	670	—	70	16	740	—	746	12	7,1
800	975	920	30	24	M27	813,0	—	—	—	24	44	—	—	770	—	70	16	842	—	850	12	7,1
900	1 075	1 020	30	24	M27	914,0	—	—	—	26	48	—	—	860	—	70	16	942	—	950	12	7,1
1 000	1 175	1 120	30	28	M27	1 016,0	—	—	—	26	52	—	—	960	—	70	16	1 045	—	1 050	16	7,1
1 200	1 405	1 340	33	32	M30	1 219,0	—	—	—	28	60	—	—	1 160	—	90	20	1 248	—	1 264	16	8,0
1 400	1 630	1 560	36	36	M33	1 422,0	—	—	—	32	68	—	—	1 346	—	90	20	1 452	—	1 480	16	8,0
1 600	1 830	1 760	36	40	M33	1 626,0	—	—	—	34	76	—	—	1 546	—	90	20	1 655	—	1 680	16	9,0
1 800	2 045	1 970	39	44	M36	1 829,0	—	—	—	36	84	—	—	1 746	—	100	20	1 855	—	1 878	16	10,0
2 000	2 265	2 180	42	48	M39	2 032,0	—	—	—	38	92	—	—	1 950	—	110	25	2 058	—	2 082	16	11,0
2 200	2 475	2 390	42	52	M39	2 235,0	—	—	—	42	—	—	—	—	—	115	25	2 260	—	—	18	12,0
2 400	2 685	2 600	42	56	M39	2 438,0	—	—	—	44	—	—	—	—	—	125	25	2 462	—	—	18	13,0
2 600	2 905	2 810	48	60	M45	2 620,0	—	—	—	46	—	—	—	—	—	130	25	2 665	—	—	18	14,0
2 800	3 115	3 020	48	64	M45	2 820,0	—	—	—	48	—	—	—	—	—	135	30	2 865	—	—	18	15,0
3 000	3 315	3 220	48	68	M45	3 020,0	—	—	—	50	—	—	—	—	—	140	30	3 068	—	—	18	16,0
3 200	3 525	3 430	48	72	M45	3 220,0	—	—	—	54	—	—	—	—	—	150	30	3 272	—	—	20	16,0
3 400	3 735	3 640	48	76	M45	3 420,0	—	—	—	56	—	—	—	—	—	160	35	3 475	—	—	20	18,0
3 600	3 970	3 860	56	80	M52	3 620,0	—	—	—	60	—	—	—	—	—	165	35	3 678	—	—	20	18,0


^a Above DN 600, dimension *C₁* shall be specified by the purchaser.
^b For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

EN 1092-1:2001 (E)

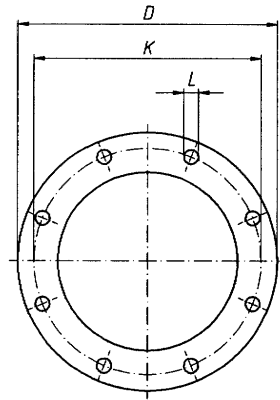


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.

Refer to the column "Bolting Number" in Table 8 for the actual number.

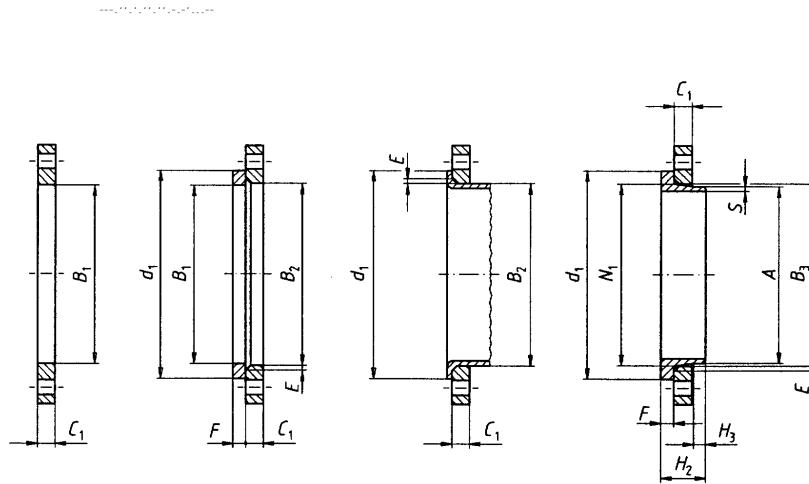

Type 01 Type 02 and 32 Type 02 and 33 Type 04 and 34

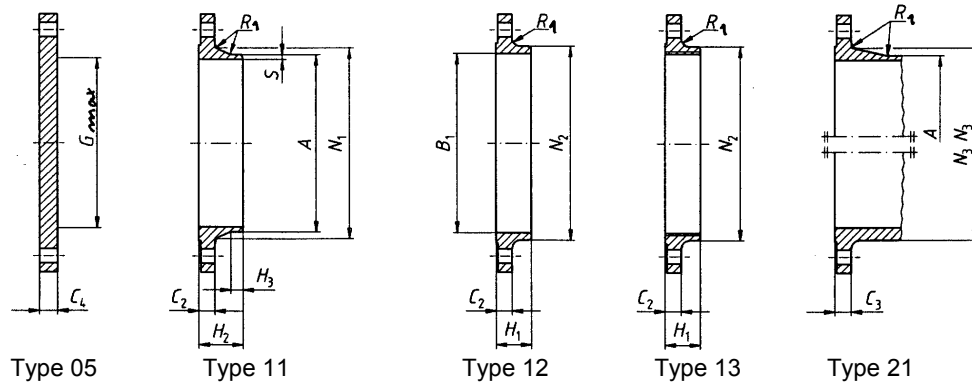

Type 05 Type 11 Type 12 Type 13 Type 21

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimensions d_1 see Table 4.

NOTE 3 For dimensions G_{max} refer to NOTE 1 of 5.6.1.

NOTE 4 Type 33; lapped pipe end without determination of thickness.

Figure 7 — Dimensions of PN 10 flanges


Table 8 — Dimensions of PN 10 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters			Flange thickness				Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulder <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>B₃</i>	<i>C₁</i>	<i>C₂</i>	<i>C₃</i>	<i>C₄</i>				<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size																			
Flange type																								
01, 02, 04, 05, 11, 12, 13, 21						11 21 ^a 34	01 12 32	02	04	01 02 04	11 12 13	21	05	02 04	32 34	05	12 13	11 34	11 34	11 34	12 13	21	11 12 13 21	11 34
10 to 40	Use PN 40 dimensions																							
50 to 150	Use PN 16 dimensions																							
200	340	295	22	8	M20	219,1	221,5	226	240	24	24	24	24	6	20	190	44	62	16	234	246	246	10	6,3
250	395	350	22	12	M20	273,0	276,5	281	294	26	26	26	26	8	22	235	46	68	16	292	298	298	12	6,3
300	445	400	22	12	M20	323,9	327,5	333	348	26	26	26	26	8	22	285	46	68	16	342	350	348	12	7,1
350	505	460	22	16	M20	335,6	359,5	365	400	28	26	26	26	8	22	330	53	68	16	385	400	408	12	7,1
400	565	515	26	16	M24	406,4	411,0	416	450	32	26	26	26	8	24	380	57	72	16	440	456	456	12	7,1
450	615	565	26	20	M24	457,0	462,0	467	498	36	28	28	28	8	24	425	63	72	16	488	502	502	12	7,1
500	670	620	26	20	M24	508,0	513,5	519	550	38	28	28	28	8	26	475	67	75	16	542	559	559	12	7,1
600	780	725	30	20	M27	610,0	616,5	622	650	42	28	34	34	8	26	575	75	80	18	642	658	658	12	7,1
700	895	840	30	24	M27	711,0	—	—	—	30	34	38	—	—	670	—	80	18	746	—	772	12	8,0	
800	1 015	950	33	24	M30	813,0	—	—	—	32	36	42	—	—	770	—	90	18	850	—	876	12	8,0	
900	1 115	1 050	33	28	M30	914,0	—	—	—	34	38	46	—	—	860	—	95	20	950	—	976	12	10,0	
1 000	1 230	1 160	36	28	M33	1 016,0	—	—	—	34	38	52	—	—	960	—	95	20	1 052	—	1 080	16	10,0	
1 200	1 455	1 380	39	32	M36	1 219,0	—	—	—	38	44	60	—	—	1 160	—	115	25	1 256	—	1 292	16	11,0	
1 400	1 675	1 590	42	36	M39	1 422,0	—	—	—	42	48	—	—	—	—	—	120	25	1 460	—	1 496	16	12,0	
1 600	1 915	1 820	48	40	M45	1 626,0	—	—	—	46	52	—	—	—	—	—	130	25	1 666	—	1 712	16	14,0	
1 800	2 115	2 020	48	44	M45	1 829,0	—	—	—	50	56	—	—	—	—	—	140	30	1 868	—	1 910	16	15,0	
2 000	2 325	2 230	48	48	M45	2 032,0	—	—	—	54	60	—	—	—	—	—	150	30	2 072	—	2 120	16	16,0	
2 200	2 550	2 440	56	52	M52	2 235,0	—	—	—	58	—	—	—	—	—	—	160	35	2 275	—	—	18	18,0	
2 400	2 760	2 650	56	56	M52	2 438,0	—	—	—	62	—	—	—	—	—	—	170	35	2 478	—	—	18	20,0	
2 600	2 960	2 850	56	60	M52	2 620,0	—	—	—	66	—	—	—	—	—	—	180	40	2 680	—	—	18	22,0	
2 800	3 180	3 070	56	64	M52	2 820,0	—	—	—	70	—	—	—	—	—	—	190	40	2 882	—	—	18	22,0	
3 000	3 405	3 290	62	68	M56	3 020,0	—	—	—	75	—	—	—	—	—	—	200	45	3 085	—	—	18	24,0	


^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

EN 1092-1:2001 (E)

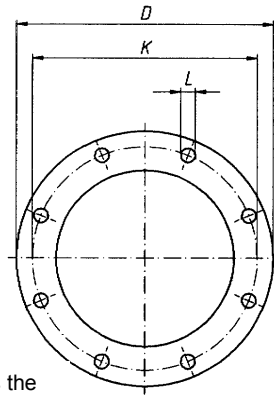


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.

Refer to the column "Bolting Number" in Table 9 for the actual number.

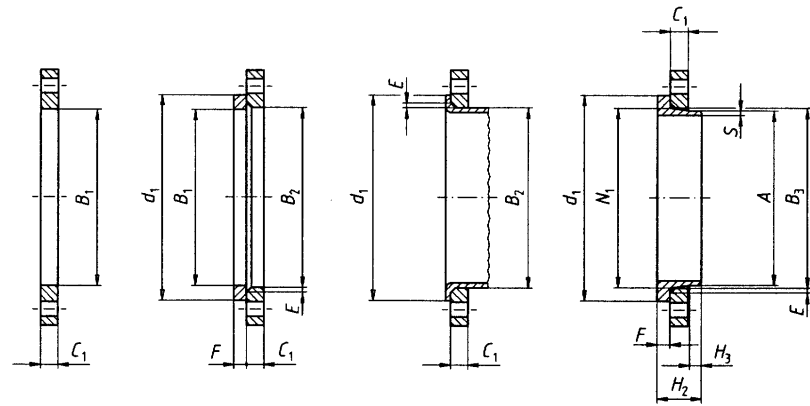

Type 01 Type 02 and 32 Type 02 and 33 Type 04 and 34

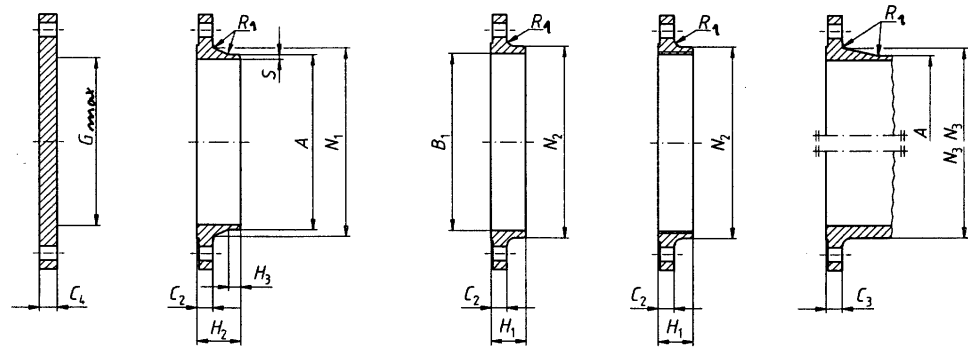

Type 05 Type 11 Type 12 Type 13 Type 21

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimensions d_1 see Table 4.

NOTE 3 For dimensions G_{max} refer to NOTE 1 of 5.6.1.

NOTE 4 Type 33; lapped pipe end without determination of thickness.

Figure 8 — Dimensions of PN 16 flanges

Table 9 — Dimensions of PN 16 flanges


Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters			Flange thickness				Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulder <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>B₃</i>	<i>C₁</i>	<i>C₂</i>	<i>C₃</i>	<i>C₄</i>				<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size																			
Flange type																								
01, 02, 04, 05, 11, 12, 13, 21					11 21 ^a 34	01 12 32	02	04	01 02 04	11 12 13	21	05	02 04	32 34	05	12 13	11 34	11 34	11 34	12 13	21	11 12 13 21	11 34	
10 to 40	Use PN 40 dimensions																							
50	165	125	18	4	M16	60,3	61,5	65	77	19	18	18	18	5	16	—	28	45	8	74	84	84	5	2,9
65	185	145	18	8 ^b	M16	76,1	77,5	81	96	20	18	18	18	6	16	55	32	45	10	92	104	104	6	2,9
80	200	160	18	8	M16	88,9	90,5	94	108	20	20	20	20	6	16	70	34	50	10	105	118	120	6	3,2
100	220	180	18	8	M16	114,3	116,0	120	134	22	20	20	20	6	18	90	40	52	12	131	140	140	8	3,6
125	250	210	18	8	M16	139,7	141,5	145	162	22	22	22	22	6	18	115	44	55	12	156	168	170	8	4,0
150	285	240	22	8	M20	168,3	170,5	174	188	24	22	22	22	6	20	140	44	55	12	184	195	190	10	4,5
200	340	295	22	12	M20	219,1	221,5	226	240	26	24	24	24	6	20	190	44	62	16	235	246	246	10	6,3
250	405	355	26	12	M24	273,0	276,5	281	294	29	26	26	26	8	22	235	46	70	16	292	298	296	12	6,3
300	460	410	26	12	M24	323,9	327,5	333	348	32	28	28	28	8	24	285	46	78	16	344	350	350	12	7,1
350	520	470	26	16	M24	355,6	359,0	365	400	35	30	30	30	8	26	330	57	82	16	390	400	410	12	8,0
400	580	525	30	16	M27	406,4	411,0	416	454	38	32	32	32	8	28	380	63	85	16	445	456	458	12	8,0
450	640	585	30	20	M27	457,0	462,0	467	500	42	40	40	40	8	30	425	68	87	16	490	502	516	12	8,0
500	715	650	33	20	M30	508,0	513,5	510	556	46	44	44	44	8	32	475	73	90	16	548	559	576	12	8,0
600	840	770	36	20	M33	610,0	616,5	622	660	52	54	54	54	8	32	575	83	95	18	652	658	690	12	8,8
700	910	840	36	24	M33	711,0	—	—	—	—	36	42	48	—	—	670	83	100	18	755	760	760	12	8,8
800	1 025	950	39	24	M36	813,0	—	—	—	—	38	42	52	—	—	770	90	105	20	855	864	862	12	10,0
900	1 125	1 050	39	28	M36	914,0	—	—	—	—	40	44	58	—	—	860	94	110	20	955	968	962	12	10,0
1 000	1 255	1 170	42	28	M39	1 016,0	—	—	—	—	42	46	64	—	—	960	100	120	22	1 058	1072	1 076	16	10,0
1 200	1 485	1 390	48	32	M45	1 219,0	—	—	—	—	48	52	76	—	—	1 160	—	130	30	1 262	—	1 282	16	12,5
1 400	1 685	1 590	48	36	M45	1 422,0	—	—	—	—	52	58	—	—	—	1 346	—	145	30	1 465	—	1 482	16	14,2
1 600	1 930	1 820	56	40	M52	1 626,0	—	—	—	—	58	64	—	—	—	1 546	—	160	35	1 668	—	1 696	16	16,0
1 800	2 130	2 020	56	44	M52	1 829,0	—	—	—	—	62	68	—	—	—	1 746	—	170	35	1 870	—	1 896	16	17,5
2 000	2 345	2 230	62	48	M56	2 032,0	—	—	—	—	66	70	—	—	—	1 950	—	180	40	2 072	—	2 100	16	20,0

^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.


^b According to EN 1092-2 (cast iron flanges) and prEN 1092-3 (copper alloy flanges), the flanges in this DN and PN may be supplied with 4 holes. Where steel flanges are required with 4 holes, these may be supplied by agreement between manufacturer and purchaser.

EN 1092-1:2001 (E)

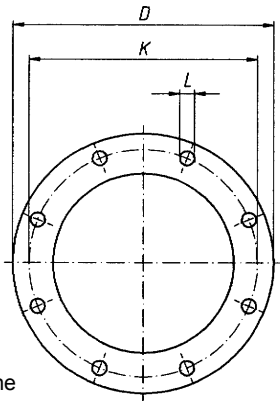

This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.

Refer to the column "Bolting Number" in Table 10 for the actual number.

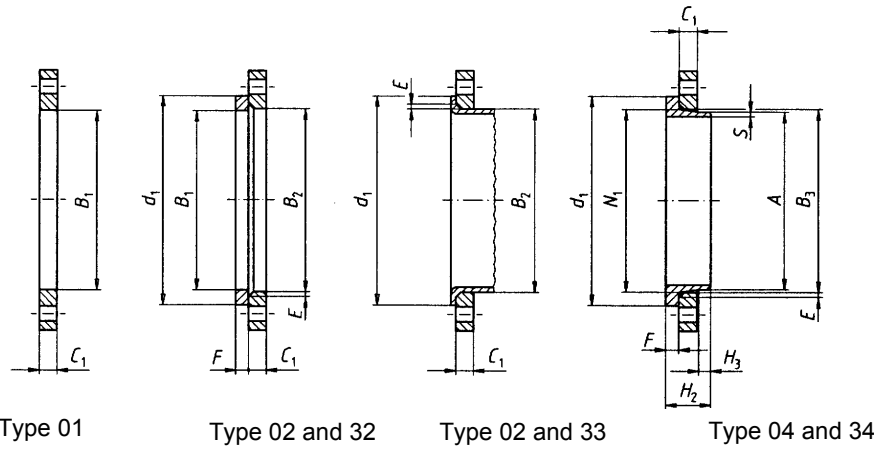


Type 01

Type 02 and 32

Type 02 and 33

Type 04 and 34

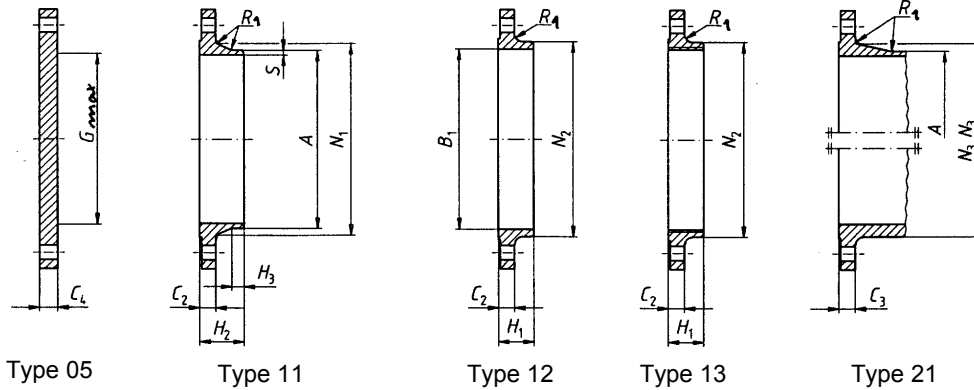

Type 05

Type 11

Type 12

Type 13

Type 21

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimensions d_1 see Table 4.

NOTE 3 For dimensions G_{max} refer to NOTE 1 of 5.6.1.

NOTE 4 Type 33; lapped pipe end without determination of thickness.

Figure 9 — Dimensions of PN 25 flanges


Table 10 — Dimensions of PN 25 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters			Flange thickness				Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulders <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>B₃</i>	<i>C₁</i>	<i>C₂</i>	<i>C₃</i>	<i>C₄</i>				<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size																			
Flange type																								
01, 02, 04, 05, 11, 12, 13, 21						11 21 ^a 34	01 12 32	02	04	01 02 04	11 12 13	21	05	02 04	32 34	05	12 13	11 34	11 34	11 34	11 12 13 21	11 12 13 21	11 34	
10 to 150	Use PN 40 dimensions																							
200	360	310	26	12	M24	219,1	221,5	226	250	32	30	30	30	6	26	190	52	80	16	244	256	252	10	6,3
250	425	370	30	12	M27	273,0	276,5	281	302	35	32	32	32	8	26	235	60	88	18	298	310	304	12	7,1
300	485	430	30	16	M27	323,9	327,5	333	356	38	34	34	34	8	28	285	67	92	18	352	364	364	12	8,0
350	555	490	33	16	M30	355,6	359,5	365	408	42	38	38	38	8	32	332	72	100	20	398	418	418	12	8,0
400	620	550	36	16	M33	406,4	411,0	416	462	46	40	40	40	8	34	380	78	110	20	452	472	472	12	8,8
450	670	600	36	20	M33	457,0	462,0	467	510	50	46	46	46	8	36	425	84	110	20	500	520	520	12	8,8
500	730	660	36	20	M33	508,0	513,5	519	568	56	48	48	48	8	38	475	90	125	20	558	580	580	12	10,0
600	845	770	39	20	M36	610,0	616,5	622	670	68	58	58	58	8	40	575	100	125	20	660	684	684	12	11,0
700	960	875	42	24	M39	711,0	—	—	—	—	46	50	—	—	—	—	—	125	20	760	—	780	12	12,5
800	1 085	990	48	24	M45	813,0	—	—	—	—	50	54	—	—	—	—	—	135	22	864	—	882	12	14,2
900	1 185	1 090	48	28	M45	914,0	—	—	—	—	54	58	—	—	—	—	—	145	24	968	—	982	12	16,0
1 000	1 320	1 210	56	28	M52	1 016,0	—	—	—	—	58	62	—	—	—	—	—	155	24	1 070	—	1 086	16	17,5
1 200	1 530	1 420	56	32	M52	1 219,0	—	—	—	—	—	70	—	—	—	—	—	—	—	—	—	1 296	18	—
1 400	1 755	1 640	62	36	M56	1 422,0	—	—	—	—	—	76	—	—	—	—	—	—	—	—	—	1 508	18	—
1 600	1 975	1 860	62	40	M56	1 626,0	—	—	—	—	—	84	—	—	—	—	—	—	—	—	—	1 726	20	—
1 800	2 195	2 070	70	44	M64	1 829,0	—	—	—	—	—	90	—	—	—	—	—	—	—	—	—	1 920	20	—
2 000	2 425	2 300	70	48	M64	2 032,0	—	—	—	—	—	96	—	—	—	—	—	—	—	—	—	2 150	20	—



^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

EN 1092-1:2001 (E)

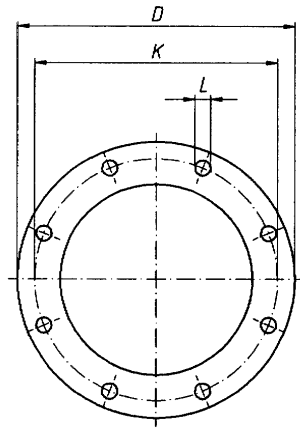

This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.

Refer to the column "Bolting Number" in Table 11 for the actual number.

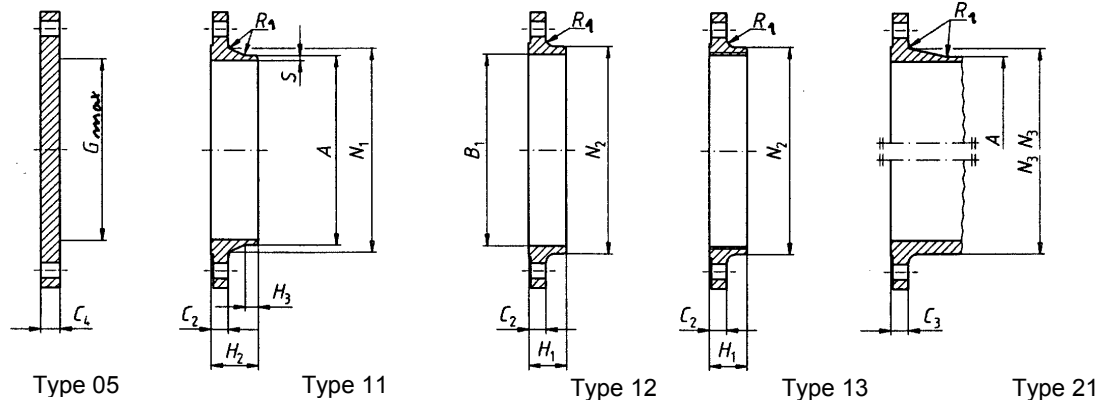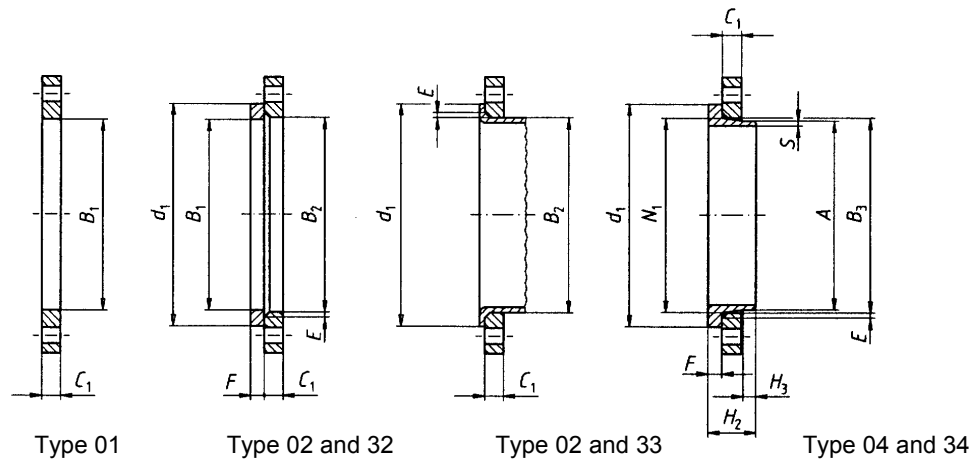

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersection of the hub draft angle and the back face of the flange.

NOTE 2 For dimensions d_1 see Table 4.

NOTE 3 For dimensions G_{max} refer to NOTE 1 of 5.6.1.

NOTE 4 Type 33; lapped pipe end without determination of thickness.

Figure 10 — Dimensions of PN 40 flanges


Table 11 — Dimensions of PN 40 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameters			Flange thickness				Chamfer <i>E</i>	Collar thickness <i>F</i>	Diameter of shoulder <i>G_{max}</i>	Length			Neck diameters			Corner radii <i>R₁</i>	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting			<i>B₁</i>	<i>B₂</i>	<i>B₃</i>	Flange thickness							<i>H₁</i>	<i>H₂</i>	<i>H₃</i>	<i>N₁</i>	<i>N₂</i>	<i>N₃</i>		
				Number	Size					<i>C₁</i>	<i>C₂</i>	<i>C₃</i>	<i>C₄</i>											
	01, 02, 04, 05, 11, 12, 13, 21						11 21 ^a 34	01 12 32	02	04	01 02 04	11 12 13	21				05	02 04	32 34	05	12 13	11 34		
10	90	60	14	4	M12	17,2	18,0	21	31	14	16	16	3	12	—	22	35	6	28	30	28	4	1,8	
15	95	65	14	4	M12	21,3	22,0	25	35	14	16	16	3	12	—	22	38	6	32	35	32	4	2,0	
20	105	75	14	4	M12	26,9	27,5	31	42	16	18	18	4	14	—	26	40	6	40	45	40	4	2,3	
25	115	85	14	4	M12	33,7	34,5	38	49	16	18	18	4	14	—	28	40	6	46	52	50	4	2,6	
32	140	100	18	4	M16	42,4	43,5	47	59	18	18	18	5	14	—	30	42	6	56	60	60	6	2,6	
40	150	110	18	4	M16	48,3	49,5	53	67	18	18	18	5	14	—	32	45	7	64	70	70	6	2,6	
50	165	125	18	4	M16	60,3	61,5	65	77	20	20	20	5	16	—	34	48	8	75	84	84	6	2,9	
65	185	145	18	8	M16	76,1	77,5	81	96	22	22	22	6	16	55	38	52	10	90	104	104	6	2,9	
80	200	160	18	8	M16	88,9	90,5	94	114	24	24	24	6	18	70	40	58	12	105	118	120	8	3,2	
100	235	190	22	8	M20	114,3	116,0	120	138	26	24	24	6	20	90	44	65	12	134	145	142	8	3,6	
125	270	220	26	8	M24	139,7	141,5	145	166	28	26	26	6	22	115	48	68	12	162	170	162	8	4,0	
150	300	250	26	8	M24	168,3	170,5	174	194	30	28	28	6	24	140	52	75	12	192	200	192	10	4,5	
200	375	320	30	12	M27	219,1	221,5	226	250	36	34	36	6	28	190	52	88	16	244	260	254	10	6,3	
250	450	385	33	12	M30	273,0	276,5	281	312	42	38	38	8	30	235	60	105	18	306	312	312	12	7,1	
300	515	450	33	16	M30	323,9	327,5	333	368	48	42	42	8	34	285	67	115	18	362	380	378	12	8,0	
350	580	510	36	16	M33	355,6	359,5	365	418	54	46	46	8	36	330	72	125	20	408	424	432	12	8,8	
400	660	585	39	16	M36	406,4	411,0	416	472	60	50	50	8	42	380	78	135	20	462	478	498	12	11,0	
450	685	610	39	20	M36	457,0	462,0	467	510	66	57	57	8	46	425	84	135	20	500	522	522	12	12,5	
500	755	670	42	20	M39	508,0	513,5	519	572	72	57	57	8	50	475	90	140	20	562	576	576	12	14,2	
600	890	795	48	20	M45	610,0	616,5	622	676	84	72	72	8	54	575	100	150	20	666	686	686	12	16,0	


^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

EN 1092-1:2001 (E)

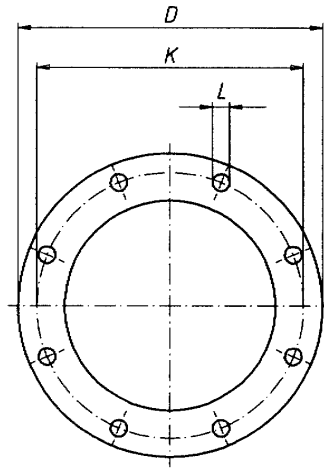


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.


Refer to the column "Bolting Number" in Table 12 for the actual number.




Type 01




Type 05

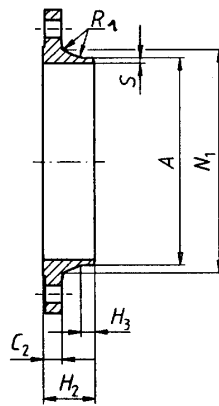


Type 11

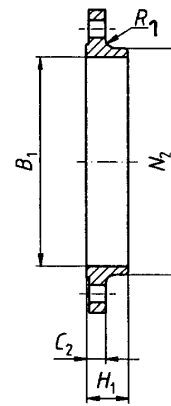

Type 12

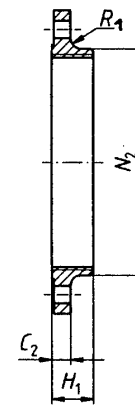

Type 13

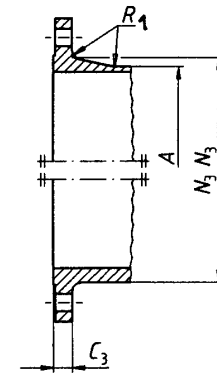

Type 21

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersections of the hub draft angle and the back face of the flange.

NOTE 2 For dimension G_{max} refer to NOTE 1 of 5.6.1.

Figure 11 — Dimensions of PN 63 flanges


Table 12 — Dimensions of PN 63 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameter <i>B</i> ₁	Flange thickness				Diameter of shoulder <i>G</i> _{max}	Length			Neck diameters			Corner radii <i>R</i> ₁	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting				<i>C</i> ₁	<i>C</i> ₂	<i>C</i> ₃	<i>C</i> ₄		<i>H</i> ₁	<i>H</i> ₂	<i>H</i> ₃	<i>N</i> ₁	<i>N</i> ₂	<i>N</i> ₃		
				Number	Size															
Flange type																				
01, 05, 11, 12, 13, 21						11 21 ^a	01 12	01	11 12 13	21	05	05	12 13	11	11	11	12 13	21	11 12 13 21	11
10 15 20 25 32 40 50 65 80 100 125 150 200 250 300 350 400 500 600 700 800 900 1 000 1 200	Use PN 100 dimensions																			
	180	135	22	4	M20	60,3	61,5	26	26	26	26	—	36	62	10	82	90	90	6	2,9
	205	160	22	8	M20	76,1	77,5	26	26	26	26	45	40	68	12	98	112	105	6	3,2
	215	170	22	8	M20	88,9	90,5	30	28	28	28	60	44	72	12	112	125	122	8	3,6
	250	200	26	8	M24	114,3	116,0	32	30	30	30	80	52	78	12	138	152	146	8	4,0
	295	240	30	8	M27	139,7	141,5	34	34	34	34	105	56	88	12	168	185	177	8	4,5
	345	280	33	8	M30	168,3	170,5	36	36	36	36	130	60	95	12	202	215	204	10	5,6
	415	345	36	12	M33	219,1	221,5	46	42	42	42	180	—	110	16	256	—	264	10	7,1
	470	400	36	12	M33	273,0	276,5	54	46	46	46	220	—	125	18	316	—	320	12	8,8
	530	460	36	16	M33	323,9	327,5	62	52	52	52	270	—	140	18	372	—	378	12	11,0
	600	525	39	16	M36	355,6	359,5	72	56	56	56	310	—	150	20	420	—	434	12	12,5
	670	585	42	16	M39	406,4	411,0	78	60	60	60	360	—	160	20	475	—	490	12	14,2
	800	705	48	20	M45	—	—	—	—	68	—	—	—	—	—	—	—	602	12	—
	930	820	56	20	M52	—	—	—	—	76	—	—	—	—	—	—	—	714	15	—
	1 045	935	56	24	M52	—	—	—	—	84	—	—	—	—	—	—	—	826	15	—
	1 165	1 050	62	24	M56	—	—	—	—	92	—	—	—	—	—	—	—	938	18	—
	1 285	1 170	62	28	M56	—	—	—	—	98	—	—	—	—	—	—	—	1 048	18	—
	1 415	1 290	70	28	M64	—	—	—	—	108	—	—	—	—	—	—	—	1 162	18	—
	1 665	1 530	78	32	M72x6	—	—	—	—	126	—	—	—	—	—	—	—	1 390	18	—


^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

EN 1092-1:2001 (E)

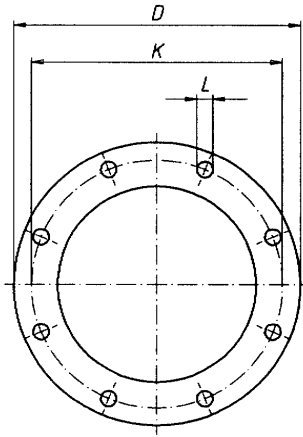


This diagram illustrates the arrangement but not necessarily the correct number of bolt holes.


Refer to the column "Bolting Number" in Table 13 for the actual number.




Type 01




Type 05

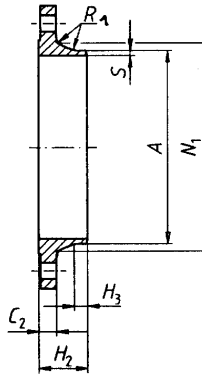


Type 11

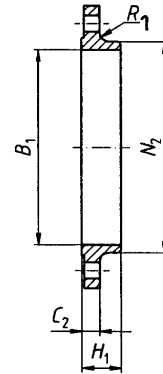

Type 12

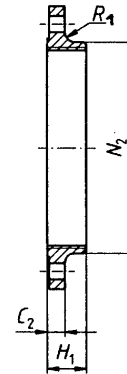

Type 13

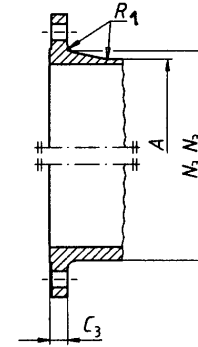

Type 21

NOTE 1 Dimensions N_1 , N_2 and N_3 are measured at the intersections of the hub draft angle and the back face of the flange.

NOTE 2 For dimension G_{max} refer to NOTE 1 of 5.6.1.

Figure 12 — Dimensions of PN 100 flanges

Table 13 — Dimensions of PN 100 flanges

Dimensions in millimetres

DN	Mating dimensions					Outside diameter of neck <i>A</i>	Bore diameter <i>B</i> ₁	Flange thickness				Diameter of shoulder <i>G</i> _{max}	Length			Neck diameters			Corner radii <i>R</i> ₁	Neck thickness (see 5.6.1) <i>S</i>
	Outside diameter <i>D</i>	Diameter of bolt circle <i>K</i>	Diameter of bolt hole <i>L</i>	Bolting				<i>C</i> ₁	<i>C</i> ₂	<i>C</i> ₃	<i>C</i> ₄		<i>H</i> ₁	<i>H</i> ₂	<i>H</i> ₃	<i>N</i> ₁	<i>N</i> ₂	<i>N</i> ₃		
				Number	Size															
Flange type																				
01, 05, 11, 12, 13, 21						11 21 ^a	01 12	01	11 12 13	21	05	05	12 13	11	11	11	12 13	21	11 12 13 21	11
10	100	70	14	4	M12	17,2	18,0	20	20	20	20	—	28	45	6	32	40	40	4	1,8
15	105	75	14	4	M12	21,3	22,0	20	20	20	20	—	28	45	6	34	43	45	4	2,0
20	130	90	18	4	M16	26,9	27,5	22	22	22	22	—	30	48	8	42	52	50	4	2,6
25	140	100	18	4	M16	33,7	34,5	24	24	24	24	—	32	58	8	52	60	61	4	2,6
32	155	110	22	4	M20	42,4	43,5	24	24	26	24	—	32	60	8	62	68	68	6	2,9
40	170	125	22	4	M20	48,3	49,5	26	26	28	26	—	34	62	10	70	80	82	6	2,9
50	195	145	26	4	M24	60,3	61,3	28	28	30	28	—	36	68	10	90	95	96	6	3,2
65	220	170	26	8	M24	76,1	77,5	30	30	34	30	45	40	76	12	108	118	118	6	3,6
80	230	180	26	8	M24	88,9	90,5	34	32	36	32	60	44	78	12	120	130	128	8	4,0
100	265	210	30	8	M27	114,3	116,0	36	36	40	36	80	52	90	12	150	158	150	8	5,0
125	315	250	33	8	M30	139,7	141,5	42	40	40	40	105	56	105	12	180	188	185	8	6,3
150	355	290	33	12	M30	168,3	170,5	48	44	44	44	130	60	115	12	210	225	216	10	7,1
200	430	360	36	12	M33	219,1	221,5	60	52	52	52	180	—	130	16	278	—	278	10	10,0
250	505	430	39	12	M36	273,0	276,5	72	60	60	60	210	—	157	18	340	—	340	12	12,5
300	585	500	42	16	M39	323,9	327,5	84	68	68	68	260	—	170	18	400	—	407	12	14,2
350	655	560	48	16	M45	355,6	359,5	95	74	74	74	300	—	189	20	460	—	460	12	16,0
400	715	620	48	16	M45	406,4	411,0	106	—	78	—	—	—	—	—	—	—	518	—	—
500	870	760	56	20	M52	508,0	513,5	128	—	94	—	—	—	—	—	—	—	630	—	—

^a For flanges type 21 the outside hub diameter approximately corresponds to the outside pipe diameter.

Table 14 — Tolerances

Dimension	Flange Type	Size	Tolerance mm
Outside diameter of neck A	11, 21, 34	\leq DN 125	+3,0 0
		$>$ DN 125 \leq DN 1200	+4,5 0
		$>$ DN 1200	+6,0 0
Bore diameter B_1, B_2, B_3	01, 02, 04, 12, 32	\leq DN 100	+0,5 0
		$>$ DN 100 \leq DN 400	+1,0 0
		$>$ DN 400 \leq DN 600	+1,5 0
		$>$ DN 600	+3,0 0
Outside diameter D	21	\leq DN 250 $>$ DN 250 \leq DN 500 $>$ DN 500 \leq DN 800 $>$ DN 800 \leq DN 1200 $>$ DN 1200 \leq DN 1600 $>$ DN 1600 \leq DN 2000 $>$ DN 2000	\pm 4,0 \pm 5,0 \pm 6,0 \pm 7,0 \pm 8,0 \pm 10,0 \pm 12,0
	All other types	\leq DN 150 $>$ DN 150 \leq DN 500 $>$ DN 500 \leq DN 1200 $>$ DN 1200 \leq DN 1800 $>$ DN 1800	\pm 2,0 \pm 3,0 \pm 5,0 \pm 7,0 \pm 10,0
Length through hub H_1, H_2, H_3	11, 12, 13	\leq DN 80 $>$ DN 80 \leq DN 250 $>$ DN 250	\pm 1,5 \pm 2,0 \pm 3,0
Neck diameter N_1, N_2, N_3	11, 21, 34	\leq DN 50 $>$ DN 50 \leq DN 150 $>$ DN 150 \leq DN 300 $>$ DN 300 \leq DN 600 $>$ DN 600 \leq DN 1200	0 -2,0 0 -4,0 0 -6,0 0 -8,0 0 -10,0
	12, 13	\leq DN 50 $>$ DN 50 \leq DN 150 $>$ DN 150 \leq DN 300 $>$ DN 300 \leq DN 600 $>$ DN 600 \leq DN 1200 $>$ DN 1200 \leq DN 1800 $>$ DN 1800	+1,0 0 +2,0 0 +4,0 0 +8,0 0 +12,0 0 +16,0 0 +20,0 0

Table 14 (continued)

Dimension		Flange type	Size	Tolerance mm
Flange thickness C_1, C_2, C_3, C_4		All types (machined on both faces)	≤ 18 mm thickness > 18 mm ≤ 50 mm thickness > 50 mm thickness	$\pm 1,0$ $\pm 1,5$ $\pm 2,0$
		All types (machined on front face only) Type 02 and 04 (unmachined)	≤ 18 mm thickness > 18 mm ≤ 50 mm thickness > 50 mm thickness	$+2,0$ $-1,3$ $+4,0$ $-1,5$ $+7,0$ $-2,0$
Facing diameter d_1		All types	\leq DN 250 $>$ DN 250	$+2,0$ $-1,0$ $+3,0$ $-1,0$
Facing height f_1		All types (facing type B, D, F and G)	2 mm	0 $-1,0$
Facing height f_2		All types (facing types C, E and G)	All DN	$+0,5$ 0
Facing height f_3		All types (facing types D and F)	All DN	$+0,5$ 0
		All types (facing type H)	All DN	$+0,2$ 0
Facing height f_4		All types (facing type H)	All DN	$+0,5$ 0
Facing	W	All types	All DN	$+0,5$ 0
	X			0 $-0,5$
	Y			$+0,5$ 0
	Z			0 $-0,5$
Diameter of bolt circle K		All types	Bolt sizes M10 to M24	$\pm 1,0$
			Bolt sizes M27 to M45	$\pm 1,5$
Centre-to-centre of adjacent bolt holes		All types	Bolt sizes M10 to M24	$\pm 1,0$
			Bolt sizes M27 to M45	$\pm 1,5$
Eccentricity of machined facing diameters		All types	\leq DN 100	1,0
			$>$ DN 100	2,0
Parallelism between bolting bearing surfaces and flange jointing faces		All types (machined bearing surfaces)	All DN	1°
		All types (unmachined bearing surfaces)		2°

Table 15 — Pressure/temperature (p/T) ratings for flanges made of ferritic steels

PN	Material group	Maximum allowable temperature <i>TS</i> in °C														
		RT ^a	100	150	200	250	300	350	400	425	450	475	500	510	520	530
		Maximum allowable pressure <i>PS</i> in bar ^b														
2,5	1E0	2,5	2,5	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	2,5	2,0	1,9	1,7	1,5	1,3	—	—	—	—	—	—	—	—	—
	2E0	2,5	2,5	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	2,5	2,2	2,0	1,9	1,8	1,6	1,5	1,4	—	—	—	—	—	—	—
	3E1	2,5	2,5	2,5	2,5	2,3	2,1	1,9	1,7	—	—	—	—	—	—	—
6	1E0	6,0	6,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	6,0	4,8	4,5	4,1	3,6	3,1	—	—	—	—	—	—	—	—	—
	2E0	6,0	6,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	6,0	5,6	5,2	4,7	4,3	3,9	3,6	3,5	—	—	—	—	—	—	—
	3E1	6,0	6,0	6,0	6,0	5,5	4,9	4,5	4,1	—	—	—	—	—	—	—
10	1E0	10,0	10,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	10,0	8,0	7,5	6,9	6,0	5,2	—	—	—	—	—	—	—	—	—
	2E0	10,0	10,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	10,0	9,3	8,7	7,8	7,1	6,4	6,0	5,8	4,5	—	—	—	—	—	—
	4E0	10,0	10,0	10,0	10,0	9,1	8,2	7,6	6,9	—	—	—	—	—	—	—
16	1E0	16,0	16,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	16,0	12,8	11,9	11,0	9,7	8,3	—	—	—	—	—	—	—	—	—
	2E0	16,0	16,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	16,0	14,9	13,9	12,4	11,4	10,3	9,6	9,2	—	—	—	—	—	—	—
	4E0	16,0	16,0	16,0	15,3	14,2	12,1	11,4	10,7	10,5	10,3	10,2	7,2	—	—	—
25	1E0	25,0	25,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	25,0	20,0	18,7	17,2	15,1	13,0	—	—	—	—	—	—	—	—	—
	2E0	25,0	25,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	25,0	23,3	21,7	19,4	17,8	16,1	15,0	14,4	—	—	—	—	—	—	—
	4E0	25,0	25,0	25,0	23,9	22,2	18,9	17,8	16,7	16,4	16,1	15,9	11,2	—	—	—
40	1E0	40,0	40,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	40,0	32,0	29,9	27,6	24,2	20,8	—	—	—	—	—	—	—	—	—
	2E0	40,0	40,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	40,0	37,3	34,7	30,2	28,4	25,8	24,0	23,1	—	—	—	—	—	—	—
	4E0	40,0	40,0	40,0	38,2	35,6	30,2	28,4	26,7	26,3	25,8	25,4	18,0	—	—	—
63	1E0	63,0	63,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	63,0	50,4	47,0	43,4	38,1	32,8	—	—	—	—	—	—	—	—	—
	2E0	63,0	63,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	63,0	58,8	54,6	47,6	44,8	40,6	37,8	36,4	—	—	—	—	—	—	—
	4E0	63,0	63,0	63,0	60,2	56,0	47,6	44,8	42,0	41,4	40,6	40,0	28,3	—	—	—
100	1E0	100,0	100,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	1E1	100,0	80,0	74,7	68,9	60,4	52,0	—	—	—	—	—	—	—	—	—
	2E0	100,0	100,0	—	—	—	—	—	—	—	—	—	—	—	—	—
	3E0	100,0	93,3	86,7	75,6	71,1	64,4	60,0	57,8	—	—	—	—	—	—	—
	4E0	100,0	100,0	100,0	95,6	88,9	75,6	71,1	66,7	65,8	64,4	63,6	44,9	—	—	—

^a -10 °C to 50 °C.

^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05,11,12,13 and 21 having nominal sizes up to and including DN 600. The p/T ratings of all other flanges shall be agreed between the manufacturer and purchaser.

Table 16 — Pressure/temperature (p/T) ratings for flanges made using material groups 7EO to 9EO

PN	Material group	Maximum allowable temperature <i>TS</i> in °C											
		RT ^a	100	150	200	250	300	350	400	450	500	550	600
		Maximum allowable pressure <i>PS</i> in bar ^b											
2,5	7E0	2,5	2,5	—	—	—	—	—	—	—	—	—	—
	7E1	2,5	2,5	—	—	—	—	—	—	—	—	—	—
	7E2	2,5	2,5	—	—	—	—	—	—	—	—	—	—
	7E3	2,5	2,3	2,1	1,9	1,7	1,6	—	—	—	—	—	—
	8E0	2,5	2,5	—	—	—	—	—	—	—	—	—	—
	8E1	2,5	2,5	—	—	—	—	—	—	—	—	—	—
	8E2	2,5	2,5	2,4	2,2	2,0	1,6	1,4	1,2	—	—	—	—
	8E3	2,5	2,5	2,5	2,5	2,5	2,4	2,2	1,9	—	—	—	—
	9E0	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	1,4	0,7
6	7E0	6,0	6,0	—	—	—	—	—	—	—	—	—	—
	7E1	6,0	6,0	—	—	—	—	—	—	—	—	—	—
	7E2	6,0	6,0	—	—	—	—	—	—	—	—	—	—
	7E3	6,0	5,6	5,1	4,5	4,1	3,7	—	—	—	—	—	—
	8E0	6,0	6,0	—	—	—	—	—	—	—	—	—	—
	8E1	6,0	6,0	—	—	—	—	—	—	—	—	—	—
	8E2	6,0	6,0	5,8	5,2	4,7	3,9	3,4	2,9	—	—	—	—
	8E3	6,0	6,0	6,0	6,0	6,0	5,8	5,2	4,5	—	—	—	—
	9E0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	3,4	1,6
10	7E0	10,0	10,0	—	—	—	—	—	—	—	—	—	—
	7E1	10,0	10,0	—	—	—	—	—	—	—	—	—	—
	7E2	10,0	10,0	—	—	—	—	—	—	—	—	—	—
	7E3	10,0	9,3	8,4	7,6	6,9	6,2	—	—	—	—	—	—
	8E0	10,0	10,0	—	—	—	—	—	—	—	—	—	—
	8E1	10,0	10,0	—	—	—	—	—	—	—	—	—	—
	8E2	10,0	10,0	9,6	8,7	7,9	6,5	5,6	4,8	—	—	—	—
	8E3	10,0	10,0	10,0	10,0	10,0	9,6	8,7	7,4	—	—	—	—
	9E0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	5,7	2,6
16	7E0	16,0	16,0	—	—	—	—	—	—	—	—	—	—
	7E1	16,0	16,0	—	—	—	—	—	—	—	—	—	—
	7E2	16,0	16,0	—	—	—	—	—	—	—	—	—	—
	7E3	16,0	14,9	13,5	12,1	11,0	10,0	—	—	—	—	—	—
	8E0	16,0	16,0	—	—	—	—	—	—	—	—	—	—
	8E1	16,0	16,0	—	—	—	—	—	—	—	—	—	—
	8E2	16,0	16,0	15,4	13,9	12,6	10,5	9,0	7,7	—	—	—	—
	8E3	16,0	16,0	16,0	16,0	16,0	15,4	13,9	11,9	—	—	—	—
	9E0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	9,1	4,2
25	7E0	25,0	25,0	—	—	—	—	—	—	—	—	—	—
	7E1	25,0	25,0	—	—	—	—	—	—	—	—	—	—
	7E2	25,0	25,0	—	—	—	—	—	—	—	—	—	—
	7E3	25,0	23,3	21,1	18,9	17,2	15,6	—	—	—	—	—	—
	8E0	25,0	25,0	—	—	—	—	—	—	—	—	—	—
	8E1	25,0	25,0	—	—	—	—	—	—	—	—	—	—
	8E2	25,0	25,0	24,0	21,8	19,7	16,3	14,1	12,0	—	—	—	—
	8E3	25,0	25,0	25,0	25,0	25,0	24,0	21,8	18,6	—	—	—	—
	9E0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	14,2	6,6
40	7E0	40,0	40,0	—	—	—	—	—	—	—	—	—	—
	7E1	40,0	40,0	—	—	—	—	—	—	—	—	—	—
	7E2	40,0	40,0	—	—	—	—	—	—	—	—	—	—
	7E3	40,0	37,3	33,8	30,2	27,6	24,9	—	—	—	—	—	—
	8E0	40,0	40,0	—	—	—	—	—	—	—	—	—	—
	8E1	40,0	40,0	—	—	—	—	—	—	—	—	—	—
	8E2	40,0	40,0	38,4	34,8	31,5	26,1	22,6	19,2	—	—	—	—
	8E3	40,0	40,0	40,0	40,0	40,0	38,4	34,8	29,7	—	—	—	—
	9E0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	28,2	10,5
63	7E0	63,0	63,0	—	—	—	—	—	—	—	—	—	—
	7E1	63,0	63,0	—	—	—	—	—	—	—	—	—	—
	7E2	63,0	63,0	—	—	—	—	—	—	—	—	—	—
	7E3	63,0	58,8	53,2	47,6	43,4	39,2	—	—	—	—	—	—
	8E0	63,0	63,0	—	—	—	—	—	—	—	—	—	—
	8E1	63,0	63,0	—	—	—	—	—	—	—	—	—	—
	8E2	63,0	63,0	60,5	54,9	49,6	41,2	35,6	30,2	—	—	—	—
	8E3	63,0	63,0	63,0	63,0	63,0	60,5	54,9	46,8	—	—	—	—
	9E0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	35,8	16,5
100	7E0	100,0	100,0	—	—	—	—	—	—	—	—	—	—
	7E1	100,0	100,0	—	—	—	—	—	—	—	—	—	—
	7E2	100,0	100,0	—	—	—	—	—	—	—	—	—	—
	7E3	100,0	93,3	84,4	75,6	68,9	62,2	—	—	—	—	—	—
	8E0	100,0	100,0	—	—	—	—	—	—	—	—	—	—
	8E1	100,0	100,0	—	—	—	—	—	—	—	—	—	—
	8E2	100,0	100,0	96,0	87,1	78,7	65,3	56,4	48,0	—	—	—	—
	8E3	100,0	100,0	100,0	100,0	100,0	96,0	87,1	74,2	—	—	—	—
	9E0	100,0	100,0	100,0	100,0	100,0	100,0	100,0	100,0	100,0	100,0	56,9	26,2

^a -10 °C to 50 °C.

^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05,11,12,13 and 21 having nominal sizes up to and including DN 600.

The p/T ratings of all other flanges shall be agreed between the manufacturer and purchaser.

Table 17 — Pressure/temperature (p/T) ratings for flanges made of austenitic and austenitic-ferritic steels, based on 0,2 % proof stress

PN	Material group	Maximum allowable temperature <i>TS</i> in °C													
		RT ^a	50	100	150	200	250	300	350	400	450	500	550	600	
		Maximum allowable pressure <i>PS</i> in bar ^b													
2.5	10E0	2,3	1,9	1,7	1,6	1,4	1,3	1,2	1,2	1,1	1,1	1,0	—	—	
	10E1	2,5	2,5	2,3	1,9	1,7	1,6	1,5	1,4	1,4	1,4	1,3	1,3	1,0	
	11E0	2,2	1,9	1,7	1,6	1,4	1,3	1,2	1,2	1,1	1,1	1,0	—	—	
	12E0	2,2	2,1	2,0	1,8	1,7	1,6	1,5	1,4	1,4	1,4	1,3	1,3	1,0	
	13E0	2,1	2,1	1,8	1,7	1,5	1,4	1,3	1,3	1,2	1,2	1,1	—	—	
	13E1	2,5	2,5	2,4	2,2	1,9	1,8	1,7	1,7	1,6	1,6	1,5	—	—	
	14E0	2,3	2,2	1,9	1,8	1,6	1,5	1,4	1,3	1,3	1,3	1,2	1,2	1,1	
	15E0	2,3	2,3	2,1	2,0	1,8	1,7	1,6	1,6	1,5	1,5	1,4	1,4	1,3	
	16E0	2,5	2,5	2,5	2,5	2,5	—	—	—	—	—	—	—	—	
	6	10E0	5,6	4,7	4,1	3,7	3,4	3,1	2,9	2,8	2,6	2,5	2,5	—	—
10E1		6,0	6,0	5,5	4,7	4,2	3,9	3,6	3,5	3,3	3,3	3,2	3,0	2,4	
11E0		5,3	4,7	4,1	3,7	3,4	3,1	2,9	2,8	2,6	2,5	2,5	—	—	
12E0		5,3	5,1	4,7	4,4	4,1	3,9	3,6	3,5	3,3	3,3	3,2	3,1	2,3	
13E0		5,1	4,9	4,4	4,0	3,7	3,4	3,2	3,0	2,9	2,8	2,7	—	—	
13E1		6,0	6,0	5,7	5,2	4,7	4,4	4,1	4,0	3,9	3,8	3,7	—	—	
14E0		5,5	5,2	4,7	4,2	3,9	3,6	3,4	3,2	3,1	3,0	2,9	2,8	2,7	
15E0		5,6	5,5	5,1	4,7	4,4	4,1	3,9	3,7	3,6	3,5	3,5	3,3	3,2	
16E0		6,0	6,0	6,0	6,0	6,0	—	—	—	—	—	—	—	—	
10		10E0	9,3	7,8	6,9	6,2	5,6	5,2	4,9	4,6	4,4	4,2	4,1	—	—
	10E1	10,0	10,0	9,1	7,8	7,0	6,4	6,0	5,8	5,6	5,4	5,3	5,1	4,0	
	11E0	8,9	7,8	6,9	6,2	5,6	5,2	4,9	4,6	4,4	4,2	4,1	—	—	
	12E0	8,9	8,4	7,8	7,3	6,9	6,4	6,0	5,8	5,6	5,4	5,3	5,1	3,8	
	13E0	8,4	8,2	7,3	6,7	6,1	5,6	5,3	5,0	4,8	4,6	4,4	—	—	
	13E1	10,0	10,0	9,6	8,7	7,8	7,3	6,9	6,7	6,4	6,3	6,1	—	—	
	14E0	9,1	8,7	7,8	7,0	6,4	6,0	5,6	5,3	5,1	5,0	4,9	4,7	4,4	
	15E0	9,3	9,1	8,4	7,8	7,3	6,9	6,4	6,2	6,0	5,9	5,8	5,6	5,3	
	16E0	10,0	10,0	10,0	10,0	10,0	—	—	—	—	—	—	—	—	
	16	10E0	14,9	12,4	11,0	10,0	9,0	8,4	7,8	7,4	7,0	6,8	6,5	—	—
10E1		16,0	16,0	14,6	12,4	11,2	10,3	9,7	9,2	8,9	8,7	8,5	8,1	6,3	
11E0		14,2	12,4	11,0	10,0	9,0	8,4	7,8	7,4	7,0	6,8	6,5	—	—	
12E0		14,2	13,5	12,5	11,7	11,0	10,3	9,7	9,2	8,9	8,7	8,5	8,2	6,1	
13E0		13,5	13,2	11,7	10,7	9,7	9,0	8,5	8,0	7,7	7,4	7,1	—	—	
13E1		16,0	16,0	15,3	13,9	12,4	11,7	11,0	10,7	10,3	10,1	9,8	—	—	
14E0		14,6	13,9	12,4	11,2	10,3	9,6	9,0	8,5	8,2	8,0	7,8	7,5	7,1	
15E0		14,9	14,6	13,5	12,5	11,7	11,0	10,3	9,6	9,2	8,9	8,5	8,2	8,5	
16E0		16,0	16,0	16,0	16,0	16,0	—	—	—	—	—	—	—	—	
25		10E0	23,3	25,0	22,8	19,4	17,4	16,1	15,1	14,4	13,9	13,6	13,2	—	—
	10E1	25,0	19,4	17,2	15,6	14,1	13,1	12,2	11,6	10,9	10,6	10,2	—	—	
	11E0	22,2	21,1	19,6	18,3	17,2	16,1	15,1	14,4	13,9	13,6	13,2	9,8	7,6	
	12E0	22,2	21,1	19,6	18,3	17,2	16,1	15,1	14,4	13,9	13,6	13,2	12,8	9,6	
	13E0	21,1	25,0	23,9	21,7	19,4	18,3	17,2	16,7	16,1	15,8	15,3	—	—	
	13E1	22,8	21,7	19,4	17,6	16,1	15,0	14,1	13,3	12,8	12,6	12,2	—	—	
	14E0	22,8	22,8	21,1	19,6	18,3	17,2	16,1	15,6	15,0	14,8	14,4	13,9	13,3	
	15E0	23,3	22,8	21,1	19,6	18,3	17,2	16,1	15,6	15,0	14,8	14,4	13,9	13,3	
	16E0	25,0	25,0	25,0	25,0	25,0	—	—	—	—	—	—	—	—	
	40	10E0	37,3	31,1	27,6	24,9	22,6	21,0	19,6	18,5	17,4	16,9	16,4	—	—
10E1		40,0	40,0	36,4	31,1	27,9	25,8	24,2	23,1	22,2	21,7	21,2	20,3	15,8	
11E0		35,6	31,1	27,6	24,9	22,6	21,0	19,6	18,5	17,4	16,9	16,4	—	—	
12E0		35,6	33,8	31,3	29,3	27,6	25,8	24,2	23,1	22,2	21,7	21,2	20,4	15,3	
13E0		33,8	32,9	29,3	26,7	24,4	22,6	21,2	20,1	19,2	18,5	17,8	—	—	
13E1		40,0	40,0	38,2	34,7	31,1	29,3	27,6	26,7	25,8	25,2	24,5	—	—	
14E0		36,4	34,7	31,1	28,1	25,8	24,0	22,6	21,3	20,4	20,1	19,6	18,7	17,8	
15E0		37,3	36,4	33,8	31,3	29,3	27,6	25,8	24,9	24,0	23,6	23,1	22,2	21,3	
16E0		40,0	40,0	40,0	40,0	40,0	—	—	—	—	—	—	—	—	
63		10E0	58,8	49,0	43,4	39,2	35,6	33,0	30,8	29,1	27,4	26,6	25,8	—	—
	10E1	63,0	63,0	57,4	49,0	44,0	40,6	38,1	36,4	35,0	34,2	33,3	31,9	24,9	
	11E0	56,0	49,0	43,4	39,2	35,6	33,0	30,8	29,1	27,4	26,6	25,8	—	—	
	12E0	56,0	53,2	49,3	46,2	43,4	40,6	38,1	36,4	35,0	34,2	33,3	32,2	24,1	
	13E0	53,2	51,8	46,2	42,0	38,4	35,6	33,3	31,6	30,2	29,1	28,0	—	—	
	13E1	63,0	63,0	60,2	54,6	49,0	46,2	43,4	42,0	40,6	39,8	38,6	—	—	
	14E0	57,4	54,6	49,0	44,2	40,6	37,8	35,6	33,6	32,2	31,6	30,8	29,4	28,0	
	15E0	58,8	57,4	53,2	49,3	46,2	43,4	40,6	39,2	37,8	37,2	36,4	35,0	33,6	
	16E0	63,0	63,0	63,0	63,0	63,0	—	—	—	—	—	—	—	—	
	100	10E0	93,3	77,8	68,9	62,2	56,4	52,4	48,9	46,2	43,6	42,2	40,9	—	—
10E1		100,0	100,0	91,1	77,8	69,8	64,4	60,4	57,8	55,6	54,2	52,9	50,7	39,6	
11E0		88,9	77,8	68,9	62,2	56,4	52,4	48,9	46,2	43,6	42,2	40,9	—	—	
12E0		88,9	84,4	78,2	73,3	68,9	64,4	60,4	57,8	55,6	54,2	52,9	51,1	38,2	
13E0		84,4	82,2	73,3	66,7	60,9	56,4	52,9	50,2	48,0	46,2	44,4	—	—	
13E1		100,0	100,0	95,6	86,7	77,8	73,3	68,9	66,7	64,4	63,1	61,3	—	—	
14E0		91,1	86,7	77,8	70,2	64,4	60,0	56,4	53,3	51,1	50,2	48,9	46,7	44,4	
15E0		93,3	91,1	84,4	78,2	73,3	68,9	64,4	62,2	60,0	59,1	57,8	55,6	53,3	
16E0		100,0	100,0	100,0	100,0	100,0	—	—	—	—	—	—	—	—	

^a -10 °C to 50 °C.

^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05,11,12,13 and 21 having nominal sizes up to and including DN 600.

The p/T ratings of all other flanges shall be agreed between the manufacturer and purchaser.

Table 18 — Pressure/temperature (p/T) ratings for flanges made of austenitic and austenitic-ferritic steels, 1 % proof stress

PN	Material group	Maximum allowable temperature T_S in °C												
		RT ^a	50	100	150	200	250	300	350	400	450	500	550	600
		Maximum allowable pressure P_S in bar ^b												
2,5	10E0	2,5	2,3	2,1	1,9	1,7	1,6	1,5	1,4	1,4	1,4	1,3	—	—
	10E1	2,5	2,5	2,5	2,3	2,1	1,9	1,9	1,8	1,7	1,7	1,7	1,6	1,0
	11E0	2,5	2,3	2,1	1,9	1,7	1,6	1,5	1,4	1,4	1,4	1,3	1,3	0,8
	12E0	2,5	2,5	2,3	2,2	2,1	1,9	1,9	1,8	1,7	1,7	1,7	1,6	1,0
	13E0	2,5	2,4	2,2	2,0	1,8	1,7	1,6	1,5	1,5	1,5	1,4	—	—
	13E1	2,5	2,5	2,5	2,5	2,3	2,2	2,1	2,0	1,9	1,9	1,9	—	—
	14E0	2,5	2,5	2,3	2,1	1,9	1,8	1,7	1,7	1,6	1,6	1,5	1,5	1,3
	15E0	2,5	2,5	2,4	2,3	2,1	2,0	1,9	1,9	1,8	1,8	1,8	1,7	1,4
	16E0	—	—	—	—	—	—	—	—	—	—	—	—	—
	6	10E0	6,0	5,6	5,1	4,5	4,1	3,9	3,6	3,4	3,3	3,3	3,2	—
10E1		6,0	6,0	6,0	5,6	5,0	4,7	4,5	4,3	4,2	4,1	4,0	3,7	2,4
11E0		6,0	5,6	5,1	4,5	4,1	3,9	3,6	3,4	3,3	3,3	3,2	3,1	2,0
12E0		6,0	6,0	5,6	5,2	4,9	4,7	4,5	4,3	4,2	4,1	4,0	3,8	2,3
13E0		6,0	5,9	5,3	4,8	4,4	4,1	3,9	3,7	3,6	3,5	3,4	—	—
13E1		6,0	6,0	6,0	6,0	5,5	5,2	4,9	4,8	4,7	4,6	4,5	—	—
14E0		6,0	6,0	5,6	5,1	4,7	4,4	4,1	4,0	3,8	3,8	3,7	3,6	3,1
15E0		6,0	6,0	5,9	5,5	5,1	4,9	4,7	4,5	4,4	4,3	4,2	4,2	3,3
16E0		—	—	—	—	—	—	—	—	—	—	—	—	—
10		10E0	10,0	9,3	8,4	7,6	6,9	6,4	6,0	5,7	5,6	5,5	5,3	—
	10E1	10,0	10,0	10,0	9,3	8,3	7,8	7,4	7,1	6,9	6,8	6,6	6,2	4,0
	11E0	10,0	9,3	8,4	7,6	6,9	6,4	6,0	5,7	5,6	5,5	5,3	5,1	3,3
	12E0	10,0	10,0	9,3	8,7	8,2	7,8	7,4	7,2	6,9	6,8	6,6	6,3	3,9
	13E0	10,0	9,8	8,9	8,0	7,3	6,8	6,4	6,2	6,0	5,8	5,7	—	—
	13E1	10,0	10,0	10,0	10,0	9,1	8,7	8,2	8,0	7,8	7,6	7,5	—	—
	14E0	10,0	10,0	9,3	8,4	7,8	7,3	6,9	6,7	6,4	6,3	6,2	6,0	5,2
	15E0	10,0	10,0	9,8	9,1	8,5	8,1	7,8	7,5	7,3	7,2	7,0	6,9	5,4
	16E0	—	—	—	—	—	—	—	—	—	—	—	—	—
	16	10E0	16,0	14,9	13,5	12,1	11,0	10,3	9,6	9,2	8,9	8,7	8,5	—
10E1		16,0	16,0	16,0	14,9	13,3	12,4	11,9	11,4	11,1	10,9	10,6	10,0	6,3
11E0		16,0	14,9	13,5	12,1	11,0	10,3	9,6	9,2	8,9	8,7	8,5	8,2	5,3
12E0		16,0	16,0	14,9	13,9	13,2	12,4	11,9	11,4	11,1	10,8	10,6	10,1	6,3
13E0		16,0	15,6	14,2	12,8	11,7	10,9	10,3	9,9	9,6	9,3	9,1	—	—
13E1		16,0	16,0	16,0	16,0	14,6	13,9	13,2	12,8	12,4	12,2	11,9	—	—
14E0		16,0	16,0	14,9	13,5	12,4	11,7	11,0	10,7	10,2	10,1	9,9	9,5	8,2
15E0		16,0	16,0	15,6	14,6	13,7	13,0	12,4	12,0	11,7	11,4	11,2	11,1	8,7
16E0		—	—	—	—	—	—	—	—	—	—	—	—	—
25		10E0	25,0	23,3	21,1	18,9	17,2	16,1	15,0	14,3	13,9	13,7	13,3	—
	10E1	25,0	25,0	25,0	23,3	20,8	19,4	18,6	17,8	17,3	17,0	16,6	15,6	9,9
	11E0	25,0	23,3	21,1	18,9	17,2	16,1	15,0	14,3	13,9	13,7	13,3	12,8	8,3
	12E0	25,0	25,0	23,3	21,7	20,6	19,4	18,6	17,9	17,3	16,9	16,6	15,8	9,8
	13E0	25,0	24,4	22,2	20,0	18,3	17,0	16,1	15,4	15,0	14,6	14,2	—	—
	13E1	25,0	25,0	25,0	25,0	22,8	21,7	20,6	20,0	19,4	19,1	18,7	—	—
	14E0	25,0	25,0	23,3	21,1	19,4	18,3	17,2	16,7	16,0	15,8	15,4	14,9	12,9
	15E0	25,0	25,0	24,4	22,8	21,3	20,3	19,4	18,8	18,2	17,9	17,6	17,3	13,6
	16E0	—	—	—	—	—	—	—	—	—	—	—	—	—
	40	10E0	40,0	37,3	33,8	30,2	27,6	25,8	24,0	22,9	22,2	21,9	21,3	—
10E1		40,0	40,0	40,0	37,3	33,2	31,1	29,7	28,4	27,7	27,2	26,5	24,9	15,8
11E0		40,0	37,3	33,8	30,2	27,6	25,8	24,0	22,9	22,2	21,9	21,3	20,4	13,3
12E0		40,0	40,0	37,3	34,7	32,9	31,1	29,7	28,6	27,7	27,0	26,5	25,2	15,6
13E0		40,0	39,1	35,6	32,0	29,3	27,2	25,8	24,7	24,0	23,3	22,8	—	—
13E1		40,0	40,0	40,0	40,0	36,4	34,7	32,9	32,0	31,1	30,6	29,9	—	—
14E0		40,0	40,0	37,3	33,8	31,1	29,3	27,6	26,7	25,6	25,2	24,7	23,8	20,6
15E0		40,0	40,0	39,1	36,4	34,1	32,5	31,1	30,0	29,2	28,6	28,1	27,7	21,7
16E0		—	—	—	—	—	—	—	—	—	—	—	—	—
63		10E0	63,0	58,8	53,2	47,6	43,4	40,6	37,8	36,1	35,0	34,4	33,6	—
	10E1	63,0	63,0	63,0	58,8	52,4	49,0	46,8	44,8	43,7	42,8	41,7	39,2	24,9
	11E0	63,0	58,8	53,2	47,6	43,4	40,6	37,8	36,1	35,0	34,4	33,6	32,2	21,0
	12E0	63,0	63,0	58,8	54,6	51,8	49,0	46,8	45,1	43,7	42,6	41,7	39,8	24,6
	13E0	63,0	61,6	56,0	50,4	46,2	42,8	40,6	38,9	37,8	36,7	35,8	—	—
	13E1	63,0	63,0	63,0	63,0	57,4	54,6	51,8	50,4	49,0	48,2	47,0	—	—
	14E0	63,0	63,0	58,8	53,2	49,0	46,2	43,4	42,0	40,3	39,8	38,9	37,5	32,5
	15E0	63,0	63,0	61,6	57,4	53,8	51,2	49,0	47,3	45,9	45,1	44,2	43,7	34,2
	16E0	—	—	—	—	—	—	—	—	—	—	—	—	—
	100	10E0	100,0	93,3	84,4	75,6	68,9	64,4	60,0	57,3	55,6	54,7	53,3	—
10E1		100,0	100,0	100,0	93,3	83,1	77,8	74,2	71,1	69,3	68,0	66,2	62,2	39,6
11E0		100,0	93,3	84,4	75,6	68,9	64,4	60,0	57,3	55,6	54,7	53,3	51,1	33,3
12E0		100,0	100,0	93,3	86,7	82,2	77,8	74,2	71,6	69,3	67,6	66,2	63,1	39,1
13E0		100,0	97,8	88,9	80,0	73,3	68,0	64,4	61,8	60,0	58,2	56,9	—	—
13E1		100,0	100,0	100,0	100,0	91,1	86,7	82,2	80,0	77,8	76,4	74,7	—	—
14E0		100,0	100,0	93,3	84,4	77,8	73,3	68,9	66,7	64,0	63,1	61,8	59,6	51,6
15E0		100,0	100,0	97,8	91,1	85,3	81,3	77,8	75,1	72,9	71,6	70,2	69,3	54,2
16E0		—	—	—	—	—	—	—	—	—	—	—	—	—

^a -10 °C to 50 °C.

^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

The p/T ratings of all other flanges shall be agreed between manufacturer and purchaser.

Table 19 — Pressure/temperature (p/T) ratings for flanges made using material groups 1C1 to 1C14

PN	Material group	Maximum allowable temperature <i>TS</i> in °C																					
		RT ^a	50	100	150	200	250	300	350	375	400	425	450	475	500	510	520	530	540	550	575	600	
		Maximum allowable pressure <i>PS</i> in bar ^b																					
2,5	1C1	2,5	2,5	2,5	2,4	2,3	2,2	2,0	2,0	1,9	1,6	1,4	0,9	0,6	0,4	—	—	—	—	—	—	—	
	1C2	2,5	2,5	2,5	2,5	2,5	2,5	2,3	2,2	2,1	1,6	1,4	0,9	0,6	0,4	—	—	—	—	—	—	—	
	1C3	2,5	2,5	2,4	2,3	2,3	2,1	2,0	1,9	1,8	1,5	1,3	0,9	0,6	0,4	—	—	—	—	—	—	—	
	1C4	2,3	2,2	2,0	2,0	1,9	1,8	1,7	1,6	1,6	1,4	1,2	0,9	0,6	0,4	—	—	—	—	—	—	—	
	1C5	2,5	2,5	2,5	2,4	2,3	2,2	2,2	2,1	2,0	1,8	1,8	1,7	1,6	1,1	—	—	—	—	—	—	—	
	1C7	2,5	2,5	2,5	2,5	2,5	2,5	2,4	2,3	2,2	2,0	2,0	1,9	1,7	1,3	1,0	0,9	0,7	0,6	0,6	—	—	
	1C9	2,5	2,5	2,5	2,5	2,5	2,5	2,4	2,3	2,3	2,2	2,2	2,1	1,7	1,2	1,0	0,9	0,8	0,7	0,6	0,4	0,2	
	1C10	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,4	2,4	2,3	1,8	1,4	1,2	1,1	0,9	0,8	0,7	0,5	0,3	
	1C13	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,4	2,4	2,3	2,2	1,5	1,0	0,9	0,8	0,7	0,6	0,5	0,4	0,3	
	1C14	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,5	2,1	1,4	1,2	1,1	0,9	0,8	0,7	0,5	0,3	
6	1C1	6,0	6,0	6,0	5,8	5,6	5,4	5,0	4,7	4,6	4,0	3,3	2,3	1,5	1,0	—	—	—	—	—	—	—	
	1C2	6,0	6,0	6,0	6,0	6,0	6,0	5,5	5,3	5,1	4,0	3,3	2,3	1,5	1,0	—	—	—	—	—	—	—	
	1C3	6,0	6,0	5,8	5,7	5,5	5,2	4,8	4,6	4,5	3,8	3,1	2,3	1,5	1,0	—	—	—	—	—	—	—	
	1C4	5,5	5,4	5,0	4,8	4,7	4,5	4,1	4,0	3,9	3,5	3,0	2,2	1,5	1,0	—	—	—	—	—	—	—	
	1C5	6,0	6,0	6,0	5,8	5,6	5,4	5,3	5,1	4,9	4,4	4,3	4,2	3,8	2,8	—	—	—	—	—	—	—	
	1C7	6,0	6,0	6,0	6,0	6,0	6,0	5,8	5,6	5,4	4,8	4,8	4,7	4,2	3,1	2,5	2,2	1,8	1,6	1,4	—	—	
	1C9	6,0	6,0	6,0	6,0	6,0	6,0	5,8	5,6	5,5	5,4	5,3	5,1	4,1	2,9	2,5	2,2	1,9	1,6	1,4	1,0	0,7	
	1C10	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	5,9	5,8	5,7	4,3	3,3	3,0	2,7	2,3	2,0	1,7	1,2	0,8	
	1C13	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	5,9	5,8	5,6	5,4	3,6	2,4	2,2	1,9	1,7	1,5	1,4	1,0	0,7
	1C14	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	6,0	5,2	3,5	3,0	2,6	2,3	1,9	1,7	1,2	0,8	
10	1C1	10,0	10,0	10,0	9,7	9,4	9,0	8,3	7,9	7,7	6,7	5,5	3,8	2,6	1,7	—	—	—	—	—	—	—	
	1C2	10,0	10,0	10,0	10,0	10,0	10,0	9,3	8,8	8,5	6,7	5,5	3,8	2,6	1,7	—	—	—	—	—	—	—	
	1C3	10,0	10,0	9,7	9,4	9,2	8,7	8,1	7,7	7,5	6,3	5,3	3,8	2,6	1,7	—	—	—	—	—	—	—	
	1C4	9,1	9,0	8,3	8,1	7,9	7,5	6,9	6,6	6,5	5,9	5,0	3,8	2,6	1,7	—	—	—	—	—	—	—	
	1C5	10,0	10,0	10,0	9,6	9,3	9,1	8,8	8,5	8,3	7,4	7,2	7,0	6,4	4,6	—	—	—	—	—	—	—	
	1C7	10,0	10,0	10,0	10,0	10,0	10,0	9,72	9,4	9,0	8,0	8,0	7,8	7,1	5,1	4,2	3,6	3,1	2,6	2,4	—	—	
	1C9	10,0	10,0	10,0	10,0	10,0	10,0	9,72	9,4	9,2	9,0	8,8	8,6	6,8	4,9	4,2	3,7	3,2	2,8	2,4	1,7	1,1	
	1C10	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	9,9	9,7	9,5	7,3	5,5	5,0	4,4	3,9	3,4	2,9	2,0	1,3	
	1C13	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	9,9	9,7	9,4	9,1	6,0	4,1	3,6	3,3	2,9	2,6	2,3	1,7	1,2	
	1C14	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	10,0	8,7	5,9	5,0	4,4	3,8	3,3	2,9	2,0	1,4	
16	1C1	16,0	16,0	16,0	15,6	15,1	14,4	13,4	12,8	12,4	10,8	8,9	6,2	4,2	2,7	—	—	—	—	—	—	—	
	1C2	16,0	16,0	16,0	16,0	16,0	16,0	14,9	14,2	13,7	10,8	8,9	6,2	4,2	2,7	—	—	—	—	—	—	—	
	1C3	16,0	16,0	15,6	15,2	14,7	14,0	13,0	12,4	12,1	10,1	8,4	6,1	4,2	2,7	—	—	—	—	—	—	—	
	1C4	14,7	14,4	13,4	13,0	12,6	12,0	11,2	10,7	10,5	9,4	8,0	6,0	4,2	2,7	—	—	—	—	—	—	—	
	1C5	16,0	16,0	16,0	15,5	15,0	14,6	14,2	13,7	13,3	11,9	11,6	11,3	10,4	7,4	—	—	—	—	—	—	—	
	1C7	16,0	16,0	16,0	16,0	16,0	16,0	15,5	15,0	14,5	12,9	12,9	12,6	11,4	8,3	6,7	5,8	5,0	4,2	3,9	—	—	
	1C9	16,0	16,0	16,0	16,0	16,0	16,0	15,5	15,0	14,8	14,5	14,1	13,8	11,0	7,9	6,8	6,0	5,2	4,5	3,9	2,7	1,8	
	1C10	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	15,9	15,6	15,3	11,7	8,9	8,0	7,1	6,2	5,4	4,7	3,2	2,1	
	1C13	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	15,9	15,6	15,1	14,6	9,6	6,6	5,8	5,3	4,7	4,1	3,7	2,7	1,9	
	1C14	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	16,0	14,0	9,4	8,0	7,1	6,1	5,3	4,6	3,2	2,2	

Table 19 (continued)

PN	Material group	Maximum allowable temperature <i>TS</i> in °C																				
		RT ^a	50	100	150	200	250	300	350	375	400	425	450	475	500	510	520	530	540	550	575	600
		Maximum allowable pressure <i>PS</i> in bar ^b																				
25	1C1	25,0	25,0	25,0	24,4	23,7	22,5	20,9	20,0	19,4	16,9	14,0	9,7	6,5	4,2	—	—	—	—	—	—	—
	1C2	25,0	25,0	25,0	25,0	25,0	25,0	23,3	22,2	21,4	16,9	14,0	9,7	6,5	4,2	—	—	—	—	—	—	—
	1C3	25,0	25,0	24,4	23,7	23,0	21,9	20,4	19,4	18,8	15,9	13,3	9,6	6,5	4,2	—	—	—	—	—	—	—
	1C4	23,0	22,5	20,9	20,4	19,7	18,8	17,5	16,7	16,5	14,8	12,6	9,5	6,5	4,2	—	—	—	—	—	—	—
	1C5	25,0	25,0	25,0	24,2	23,4	22,8	22,1	21,4	20,8	18,6	18,2	17,7	16,2	11,7	—	—	—	—	—	—	—
	1C7	25,0	25,0	25,0	25,0	25,0	25,0	24,3	23,5	22,7	20,1	20,1	19,7	17,9	13,0	10,6	9,2	7,8	6,6	6,1	—	—
	1C9	25,0	25,0	25,0	25,0	25,0	25,0	24,3	23,5	23,1	22,7	22,1	21,5	17,1	12,5	10,7	9,4	8,2	7,0	6,1	4,2	2,9
	1C10	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	24,8	24,4	23,9	18,3	14,0	12,6	11,2	9,8	8,5	7,4	5,1	3,3
	1C13	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	24,9	24,3	23,6	22,8	15,1	10,4	9,1	8,2	7,3	6,5	5,8	4,3	3,0
	1C14	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	25,0	21,9	14,8	12,6	11,2	9,6	8,2	7,2	5,0	3,4
40	1C1	40,0	40,0	40,0	39,1	37,9	36,0	33,5	31,9	31,1	27,0	22,4	15,6	10,5	6,8	—	—	—	—	—	—	—
	1C2	40,0	40,0	40,0	40,0	40,0	40,0	37,2	35,6	34,2	27,0	22,4	15,6	10,5	6,8	—	—	—	—	—	—	—
	1C3	40,0	40,0	39,0	38,0	36,9	35,1	32,6	31,1	30,1	25,4	21,2	15,4	10,5	6,8	—	—	—	—	—	—	—
	1C4	36,8	36,1	33,5	32,6	31,6	30,1	27,9	26,7	26,3	23,7	20,1	15,2	10,5	6,8	—	—	—	—	—	—	—
	1C5	40,0	40,0	40,0	38,7	37,4	36,5	35,4	34,3	33,3	29,8	29,1	28,3	26,0	18,7	—	—	—	—	—	—	—
	1C7	40,0	40,0	40,0	40,0	40,0	40,0	38,9	37,6	36,3	32,2	32,2	31,6	28,6	20,7	16,9	14,7	12,5	10,7	9,8	—	—
	1C9	40,0	40,0	40,0	40,0	40,0	40,0	38,9	37,6	36,9	36,2	35,4	34,5	27,4	19,9	17,1	15,1	13,1	11,3	9,8	6,8	4,7
	1C10	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	39,7	39,0	38,3	29,2	22,3	20,2	18,0	15,7	13,6	12,0	8,1	5,3
	1C13	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	39,8	38,9	37,8	36,4	24,1	16,6	14,7	13,3	11,8	10,4	9,3	6,9	4,8
	1C14	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	40,0	35,0	23,7	20,2	17,8	15,5	13,3	11,7	8,1	5,5
63	1C1	63,0	63,0	63,0	61,5	59,6	56,8	52,7	50,3	49,0	42,5	35,2	24,5	16,6	10,8	—	—	—	—	—	—	—
	1C2	63,0	63,0	63,0	63,0	63,0	63,0	58,7	56,0	53,8	42,5	35,2	24,5	16,6	10,8	—	—	—	—	—	—	—
	1C3	63,0	63,0	61,4	59,8	58,1	55,2	51,3	48,9	47,5	40,0	33,4	24,3	16,6	10,8	—	—	—	—	—	—	—
	1C4	57,9	56,8	52,7	51,3	49,8	47,4	44,0	42,1	41,5	37,4	31,7	24,0	16,6	10,8	—	—	—	—	—	—	—
	1C5	63,0	63,0	63,0	61,0	58,9	57,4	55,7	54,0	52,4	46,9	45,8	44,5	40,9	29,5	—	—	—	—	—	—	—
	1C7	63,0	63,0	63,0	63,0	63,0	63,0	61,2	59,2	57,2	50,7	50,7	49,7	45,0	32,7	26,6	23,2	19,8	16,8	15,4	—	—
	1C9	63,0	63,0	63,0	63,0	63,0	63,0	61,2	59,2	58,1	57,1	55,7	54,3	43,2	31,4	26,9	23,8	20,7	17,8	15,6	10,8	7,4
	1C10	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	62,5	61,5	60,3	46,0	35,2	31,9	28,3	24,8	21,4	18,8	12,9	8,4
	1C13	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	62,7	61,3	59,6	57,3	37,9	26,1	23,2	20,9	18,6	16,4	14,8	10,9	7,6
	1C14	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	63,0	55,1	37,3	31,9	28,1	24,3	20,9	18,4	12,8	8,7
100	1C1	100	100	100	97,7	94,7	90,1	83,6	79,8	77,8	67,5	55,9	38,9	26,3	17,1	—	—	—	—	—	—	—
	1C2	100	100	100	100	100	100	93,1	88,9	85,4	67,5	55,9	38,9	26,3	17,1	—	—	—	—	—	—	—
	1C3	100	100	97,4	94,9	92,2	87,6	81,4	77,7	75,3	63,4	53,1	38,5	26,3	17,1	—	—	—	—	—	—	—
	1C4	91,9	90,2	83,7	81,5	79,0	75,2	69,8	66,8	65,8	59,3	50,3	38,1	26,3	17,1	—	—	—	—	—	—	—
	1C5	100	100	100	96,8	93,5	91,2	88,5	85,7	83,2	74,4	72,8	70,7	64,9	46,8	—	—	—	—	—	—	—
	1C7	100	100	100	100	100	100	97,2	94,0	90,8	80,4	80,4	78,9	71,5	51,9	42,3	36,8	31,4	26,6	24,5	—	—
	1C9	100	100	100	100	100	100	97,2	94,0	92,3	90,6	88,4	86,2	68,6	49,9	42,7	37,8	32,8	28,2	24,7	17,1	11,8
	1C10	100	100	100	100	100	100	100	100	100	99,2	97,6	95,6	73,1	55,9	50,6	44,9	39,3	34,0	29,9	20,5	13,4
	1C13	100	100	100	100	100	100	100	100	99,6	97,3	94,6	91,0	60,2	41,4	36,8	33,1	29,5	26,1	23,4	17,3	12,1
	1C14	100	100	100	100	100	100	100	100	100	100	100	100	87,5	59,2	50,6	44,6	38,6	33,1	29,2	20,3	14,0

^a -10°C to 50 °C.

^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

The p/T ratings of all other flanges shall be agreed between manufacturer and purchaser.

Table 20 — Pressure ratings (p/T) ratings for PN flanges made using material groups 2C1 to 2C7

PN	Material Group	Maximum allowable temperature <i>TS</i> in °C																					
		RT ^a	50	100	150	200	250	300	350	375	400	425	450	475	500	510	520	530	540	550	575	600	
		Maximum allowable pressure <i>PS</i> in bar ^b																					
2,5	2C1	2,3	2,2	1,8	1,7	1,6	1,5	1,4	1,3	1,3	1,3	1,2	1,2	1,2	1,2	1,2	1,2	1,1	1,1	1,0	0,8		
	2C2	2,3	2,2	1,9	1,7	1,6	1,5	1,4	1,4	1,3	1,3	1,3	1,3	1,3	1,3	1,3	1,3	1,3	1,3	1,2	1,2	0,9	
	2C3	1,9	1,8	1,6	1,4	1,3	1,2	1,1	1,1	1,0	1,0	1,0	1,0	—	—	—	—	—	—	—	—	—	
	2C4	2,3	2,2	2,0	1,9	1,7	1,6	1,5	1,5	1,4	1,4	1,4	1,4	1,4	1,4	1,3	1,3	1,3	1,3	1,3	1,2	0,9	
	2C5	2,3	2,2	2,0	1,9	1,8	1,7	1,6	1,6	1,5	1,5	1,5	1,5	1,5	1,5	1,5	1,5	1,5	1,5	1,4	1,2	0,9	
	2C6	2,1	2,1	1,9	1,8	1,7	1,6	1,5	1,4	1,4	1,4	1,4	1,3	1,3	1,3	1,3	1,2	1,2	1,1	1,1	1,0	0,9	0,7
	2C7	2,1	2,1	1,9	1,8	1,7	1,6	1,5	1,4	1,4	1,4	1,4	1,3	1,3	1,3	1,3	1,2	1,2	1,1	1,1	1,0	0,8	
6	2C1	5,5	5,3	4,5	4,1	3,8	3,6	3,4	3,2	3,2	3,1	3,0	3,0	2,9	2,9	2,9	2,9	2,8	2,8	2,7	2,4	1,9	
	2C2	5,5	5,3	4,6	4,2	3,9	3,7	3,5	3,3	3,3	3,2	3,2	3,2	3,1	3,1	3,1	3,1	3,1	3,1	3,1	2,8	2,3	
	2C3	4,6	4,4	3,8	3,4	3,1	2,9	2,8	2,6	2,6	2,5	2,5	2,4	—	—	—	—	—	—	—	—	—	
	2C4	5,5	5,3	4,9	4,5	4,2	4,0	3,7	3,6	3,5	3,5	3,4	3,4	3,3	3,3	3,3	3,3	3,3	3,3	3,2	2,9	2,3	
	2C5	5,5	5,4	5,0	4,7	4,4	4,1	3,9	3,8	3,7	3,7	3,7	3,7	3,7	3,7	3,7	3,6	3,6	3,6	3,5	3,0	2,3	
	2C6	5,1	5,0	4,6	4,3	4,1	3,9	3,7	3,5	3,4	3,4	3,4	3,3	3,2	3,2	3,1	3,1	2,9	2,8	2,7	2,5	2,1	1,6
	2C7	5,1	5,0	4,6	4,3	4,1	3,9	3,7	3,5	3,4	3,4	3,3	3,2	3,2	3,1	3,1	3,0	2,9	2,8	2,7	2,5	1,9	
10	2C1	9,1	8,8	7,5	6,8	6,3	6,0	5,6	5,4	5,4	5,2	5,1	5,0	4,9	4,9	4,8	4,8	4,7	4,6	4,0	3,2		
	2C2	9,1	8,9	7,8	7,1	6,6	6,1	5,8	5,6	5,5	5,4	5,4	5,3	5,3	5,2	5,2	5,2	5,2	5,1	5,1	4,7	3,8	
	2C3	7,6	7,4	6,3	5,7	5,3	4,9	4,6	4,4	4,3	4,2	4,2	4,1	—	—	—	—	—	—	—	—	—	
	2C4	9,1	8,9	8,1	7,5	7,0	6,6	6,3	6,0	5,9	5,8	5,7	5,7	5,6	5,6	5,5	5,5	5,5	5,5	5,4	4,9	3,9	
	2C5	9,1	9,0	8,3	7,8	7,3	6,9	6,6	6,4	6,3	6,2	6,2	6,2	6,1	6,1	6,1	6,1	6,1	6,0	5,8	5,0	3,8	
	2C6	8,5	8,3	7,6	7,2	6,8	6,5	6,1	5,9	5,8	5,6	5,5	5,4	5,3	5,2	5,1	4,9	4,7	4,5	4,2	3,5	2,8	
	2C7	8,5	8,4	7,6	7,2	6,8	6,5	6,2	5,9	5,8	5,7	5,5	5,4	5,3	5,2	5,2	5,0	4,8	4,7	4,6	4,1	3,2	
16	2C1	14,7	14,2	12,1	11,0	10,2	9,6	9,0	8,7	8,6	8,4	8,2	8,1	7,9	7,8	7,7	7,7	7,6	7,5	7,3	6,4	5,2	
	2C2	14,7	14,3	12,5	11,4	10,6	9,8	9,3	9,0	8,8	8,7	8,6	8,5	8,5	8,4	8,3	8,3	8,3	8,3	8,2	7,6	6,1	
	2C3	12,3	11,8	10,2	9,2	8,5	7,9	7,4	7,1	6,9	6,8	6,7	6,5	—	—	—	—	—	—	—	—	—	
	2C4	14,7	14,4	13,1	12,1	11,3	10,7	10,1	9,7	9,4	9,3	9,2	9,1	9,0	8,9	8,9	8,8	8,8	8,8	8,7	7,9	6,3	
	2C5	14,7	14,4	13,4	12,5	11,8	11,2	10,6	10,2	10,1	10,0	9,9	9,9	9,8	9,8	9,8	9,8	9,8	9,7	9,4	8,1	6,1	
	2C6	13,7	13,4	12,3	11,6	10,9	10,4	9,9	9,4	9,2	9,1	8,8	8,7	8,5	8,3	8,2	7,9	7,5	7,2	6,8	5,7	4,5	
	2C7	13,7	13,4	12,3	11,6	11,0	10,5	9,9	9,5	9,2	9,1	8,9	8,7	8,5	8,4	8,3	8,0	7,7	7,5	7,4	6,6	5,2	

Table 20 (continued)

PN	Material group	Maximum allowable temperature <i>TS</i> in °C																				
		RT ^a	50	100	150	200	250	300	350	375	400	425	450	475	500	510	520	530	540	550	575	600
		Maximum allowable pressure <i>PS</i> in bar ^b																				
25	2C1	23,0	22,1	18,9	17,2	16,0	15,0	14,2	13,7	13,5	13,2	12,9	12,7	12,5	12,3	12,2	12,1	12,0	11,9	11,5	10,1	8,2
	2C2	23,0	22,3	19,5	17,8	16,5	15,5	14,6	14,1	13,8	13,6	13,5	13,4	13,3	13,2	13,1	13,1	13,0	13,0	12,9	12,0	9,6
	2C3	19,2	18,5	16,0	14,5	13,3	12,4	11,7	11,1	10,9	10,7	10,5	10,3	—	—	—	—	—	—	—	—	—
	2C4	23,0	22,5	20,4	19,0	17,7	16,7	15,8	15,2	14,8	14,6	14,4	14,3	14,1	14,0	13,9	13,9	13,8	13,8	13,6	12,4	9,8
	2C5	23,0	22,6	20,9	19,6	18,4	17,4	16,6	16,0	15,8	15,7	15,6	15,5	15,4	15,4	15,4	15,4	15,3	15,2	14,7	12,7	9,6
	2C6	21,5	21,0	19,2	18,1	17,1	16,3	15,5	14,8	14,5	14,2	13,9	13,6	13,3	13,1	12,9	12,4	11,8	11,2	10,7	8,9	7,0
	2C7	21,5	21,0	19,2	18,1	17,2	16,3	15,6	14,8	14,5	14,3	14,0	13,7	13,4	13,1	13,0	12,6	12,2	11,8	11,6	10,4	8,1
40	2C1	36,8	35,4	30,3	27,5	25,5	24,1	22,7	21,9	21,6	21,2	20,6	20,3	19,9	19,6	19,5	19,4	19,2	19,0	18,4	16,2	13,1
	2C2	36,8	35,6	31,3	28,5	26,4	24,7	23,4	22,6	22,1	21,8	21,6	21,4	21,2	21,0	21,0	20,9	20,8	20,8	20,7	19,1	15,5
	2C3	30,6	29,6	25,5	23,1	21,2	19,8	18,7	17,8	17,5	17,1	16,8	16,5	—	—	—	—	—	—	—	—	—
	2C4	36,8	35,9	32,7	30,3	28,4	26,7	25,3	24,2	23,7	23,4	23,1	22,8	22,6	22,4	22,3	22,2	22,1	22,0	21,8	19,9	15,8
	2C5	36,8	36,1	33,4	31,3	29,5	27,9	26,6	25,6	25,2	25,1	24,9	24,8	24,7	24,6	24,6	24,6	24,6	24,3	23,5	20,4	15,4
	2C6	34,3	33,6	30,7	29,0	27,4	26,0	24,8	23,7	23,2	22,8	22,2	21,8	21,3	20,9	20,7	19,8	18,9	18,0	17,1	14,4	11,3
	2C7	34,3	33,6	30,8	29,0	27,5	26,1	24,9	23,8	23,2	22,9	22,3	21,9	21,5	21,0	20,8	20,2	19,5	18,9	18,5	16,6	13,0
63	2C1	57,9	55,8	47,7	43,4	40,2	37,9	35,8	34,5	34,0	33,3	32,5	31,9	31,4	30,9	30,7	30,5	30,3	29,9	29,0	25,5	20,7
	2C2	57,9	56,1	49,2	44,9	41,6	38,9	36,9	35,5	34,9	34,4	34,0	33,7	33,5	33,2	33,0	32,9	32,8	32,7	32,6	30,2	24,4
	2C3	48,3	46,6	40,2	36,4	33,5	31,1	29,5	28,1	27,5	27,0	26,5	26,0	—	—	—	—	—	—	—	—	—
	2C4	57,9	56,6	51,4	47,8	44,7	42,0	39,8	38,2	37,4	36,8	36,3	36,0	35,6	35,3	35,1	35,0	34,9	34,7	34,4	31,3	24,8
	2C5	57,9	56,8	52,6	49,4	46,4	43,9	41,9	40,3	39,7	39,6	39,2	39,0	38,9	38,8	38,8	38,7	38,7	38,3	37,0	32,1	24,3
	2C6	54,1	52,9	48,3	45,7	43,1	41,0	39,0	37,3	36,6	35,9	35,0	34,3	33,6	32,9	32,6	31,2	29,8	28,3	26,9	22,6	17,8
	2C7	54,1	52,9	48,5	45,7	43,3	41,2	39,2	37,4	36,6	36,1	35,2	34,5	33,8	33,1	32,8	31,8	30,7	29,7	29,2	26,2	20,5
100	2C1	91,9	88,6	75,7	68,8	63,9	60,2	56,8	54,7	54,0	52,9	51,6	50,7	49,9	49,1	48,7	48,4	48,0	47,5	46,0	40,5	32,8
	2C2	91,9	89,1	78,1	71,3	66,0	61,8	58,5	56,4	55,3	54,5	54,0	53,4	53,1	52,6	52,4	52,2	52,1	51,9	51,7	47,9	38,7
	2C3	76,6	74,0	63,9	57,8	53,1	49,4	46,8	44,5	43,7	42,9	42,0	41,2	—	—	—	—	—	—	—	—	—
	2C4	91,9	89,8	81,6	75,9	70,9	66,7	63,2	60,6	59,3	58,5	57,6	57,1	56,5	56,0	55,8	55,6	55,3	55,1	54,5	49,7	39,4
	2C5	91,9	90,2	83,6	78,4	73,6	69,7	66,5	64,0	63,1	62,8	62,2	62,0	61,7	61,6	61,6	61,5	61,4	60,8	58,8	50,9	38,5
	2C6	85,8	83,9	76,7	72,5	68,4	65,0	61,9	59,2	58,0	56,9	55,6	54,4	53,3	52,2	51,8	49,5	47,2	45,0	42,7	35,9	28,2
	2C7	85,8	84,0	76,9	72,5	68,7	65,3	62,2	59,4	58,1	57,2	55,9	54,8	53,6	52,5	52,1	50,4	48,7	47,2	46,3	41,6	32,6

^a -10 °C to 50 °C.


^b 1 bar = 100 kPa.

NOTE The p/T ratings apply only for flange types 05, 11, 12, 13 and 21 having nominal sizes up to and including DN 600.

The p/T ratings of all other flanges shall be agreed between manufacturer and purchaser.

Table 21 — Minimum hub radius after back facing

Flange size	R_2 min. mm
Up to and including DN 50	2
Over DN 50 and up to including DN 200	3
Over DN 200	5

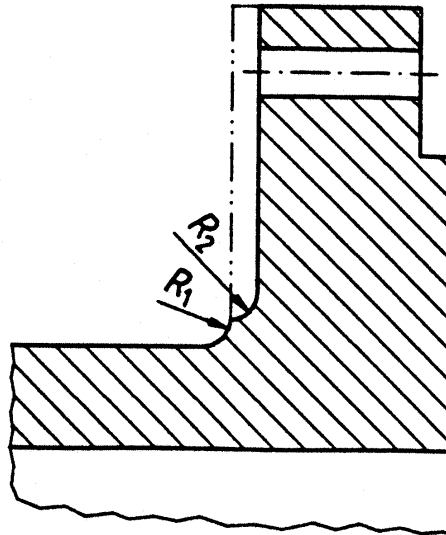

NOTE For dimensions of R_1 see Tables 6 to 13.

Figure 13 — Minimum hub radius after back facing

Annex A (normative)

Butt weld-end preparation

Unless otherwise specified, for flanges in accordance with this European Standard the welding end connections given in Figures A.1 to A.3 shall be used. Additional types of welding ends are specified in EN 29692 and example of designs in EN 1708-1 and may be used by agreement between the equipment manufacturer and the flange manufacturer.

Dimensions in millimetres

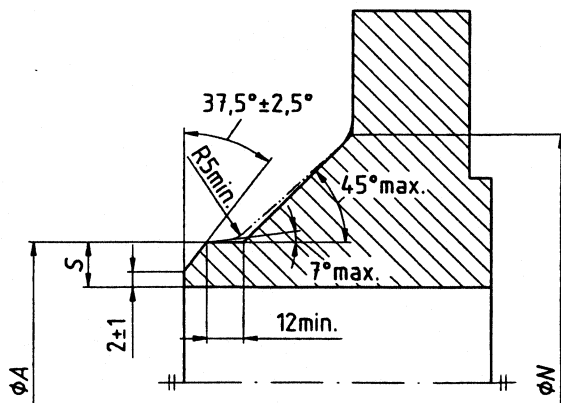


Figure A.1 — Welding end connection for wall thickness S 5 mm to 22,2 mm

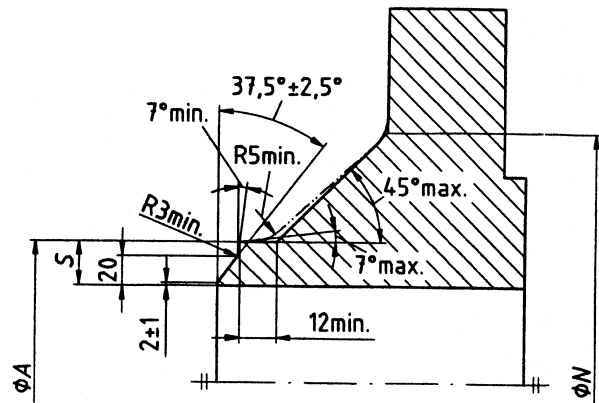


Figure A.2 — Welding end connection for wall thickness S \geq 22,2 mm

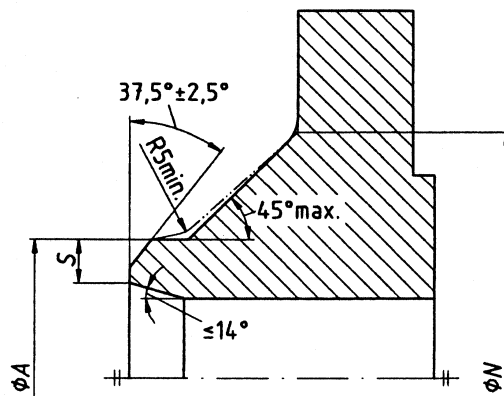


Figure A.3 — Permissible bevel design for unequal wall thickness

NOTE 1 For flanges required to connect to ferritic steel pipe of nominal wall thickness less than 4,8 mm the welding ends should be finished to a slight chamfer or be square, at the option of the manufacturer.

NOTE 2 For flanges required to connect to austenitic stainless steel pipe of nominal wall thickness 3,2 mm or less, the welding ends should be finished to a slight chamfer.

NOTE 3 The wall thickness of the flange, which connects to the pipe, should not be less than the pipe thickness or be more than 3 mm thicker.

Annex B
(informative)

Material groups

The material groups contain materials of similar chemical/mechanical properties and corrosion resistance in order to facilitate an equivalent application of materials in a group depending on pressure, temperature and fluid.

The material groups 1E0 to 6E1 were part of several European national standards and can be described as follows:

- 1E0 unalloyed structural steels without guaranteed thermal-temperature strength, application range -10 °C to $+100\text{ °C}$;
- 1E1 unalloyed structural steels with thermal-temperature strength according to AD-Merkblatt W1, July 1995, table 4, application range -10 °C to 300 °C ;
- 2E0 unalloyed steels without guaranteed thermal-temperature strength, application range 350 °C up to 400 °C ;
- 3E0 unalloyed steels with guaranteed thermal-temperature strength, application range up to 400 °C ;
- 4E0 low alloyed steels with 0,3 % molybdenum;
- 5E0 low alloyed steels with 1 % chromium and 0,5 % molybdenum;
- 6E0 low alloyed steels with 2 % chromium and 1 % molybdenum;
- 6E1 alloy steel with 5 % chromium and 0,5 % molybdenum.

The following groups of materials contain steels with low temperature toughness:

- 7E0 low-temperature-tough fine-grain steel with a minimum yield strength of 315 N/mm^2 at room temperature;
- 7E1 low-temperature-tough fine-grain steel with a minimum yield strength of 380 N/mm^2 at room temperature;
- 7E2 low-temperature high alloy nickel steel;
- 7E3 low temperature steels with strength values for elevated temperatures according to AD-Merkblatt W10, November 1987, table 3a, application range up to 300 °C .

The following groups of materials contain creep-resistant fine-grain steels, differentiating only in strength:

- 8E0 yield strength 225 N/mm² min. at room temperature;
- 8E1 yield strength 285 N/mm² min. at room temperature;
- 8E2 yield strength 315 N/mm² min. at room temperature;
- 8E3 yield strength 355 N/mm² min. at room temperature;
- 9E0 high-temperature-tough ferritic steel with 12 % chromium, 1 % molybdenum and 0,5 % vanadium.

The following groups contain austenitic stainless steels, with differences in corrosion resistance, weldability and strength, Groups 10E0 up to 12E0 are free of molybdenum, groups 13E0 to 15E0 are alloyed with molybdenum:

- 10E0 extra low carbon steel (ELC-steel);
- 10E1 ELC-steel, nitrogen-alloyed;
- 11E0 standard carbon-content;
- 12E0 alloyed with elements which form extra stable carbides;
- 13E0 extra low carbon steel with molybdenum;
- 13E1 extra low carbon steel with molybdenum and nitrogen alloyed;
- 14E0 standard carbon-content alloyed with molybdenum;
- 15E0 alloyed with molybdenum and elements which form extra stable carbides;
- 16E0 austenitic-ferritic steels.

Annex C
(informative)

Approximate masses of flanges and collars

Tables C.1 to C.8 give calculated masses of flanges and ancillary components, which may be used for guidance only.

These calculated masses are based on nominal dimensions given in Tables 6 to 13, and on densities of 7,80 g/cm³ for steel materials.

The actual masses may vary from the calculated masses due to dimensional variations within the permitted tolerances given in Table 14.

Table C.1 — Masses of flanges PN 2,5

Masses in kilograms			
DN	Type 01	Type 05	Type 11
1 200	101,5	505,0	77,5
1 400	128,0	724,5	89,5
1 600	171,0	996,0	117,5
1 800	202,5	1305,5	135,0
2 000	240,5	1699,5	153,0
2 200	—	—	196,0
2 400	—	—	213,0
2 600	—	—	230,5
2 800	—	—	283,5
3 000	—	—	304,5
3 200	—	—	324,5
3 400	—	—	365,5
3 600	—	—	410,5
3 800	—	—	457,0
4 000	—	—	480,5

Table C.2 — Masses of flanges PN 6

DN	Masses in kilograms					
	Type 01	Type 02	Type 05	Type 11	Type 12	Type 32
10	0,5	0,5	0,5	0,5	0,5	0,5
15	0,5	0,5	0,5	0,5	0,5	0,5
20	0,5	0,57	0,5	0,5	0,5	0,5
25	0,5	0,5	1,0	1,0	1,0	0,5
32	1,0	1,0	1,0	1,0	1,0	0,5
40	1,5	1,5	1,5	1,5	1,5	0,5
50	1,5	1,5	1,5	1,5	1,5	0,5
65	2,0	2,0	2,0	2,0	2,0	0,5
80	3,0	3,0	3,5	3,0	3,0	0,5
100	3,5	3,0	4,0	3,5	3,0	1,0
125	4,5	4,0	6,0	4,5	4,5	1,0
150	5,0	4,5	7,5	5,5	5,0	1,0
200	7,0	6,5	12,5	8,0	7,0	1,5
250	9,0	8,5	18,5	11,5	9,0	2,5
300	12,0	11,5	25,5	15,0	12,0	3,0
350	17,0	16,0	32,0	19,5	—	5,0
400	20,0	19,0	38,5	22,0	—	6,0
450	24,5	23,5	51,0	25,0	—	7,0
500	26,5	25,5	60,03	29,5	—	8,5
600	35,0	33,5	103,0	43,0	—	9,5
700	—	—	178,5	43,5	—	—
800	—	—	252,0	52,0	—	—
900	—	—	335,5	61,5	—	—
1 000	—	—	434,5	67,0	—	—
1 200	—	—	717,5	105,5	—	—
1 400	—	—	1094,0	149,0	—	—
1 600	—	—	1545,0	181,5	—	—
1 800	—	—	2131,0	235,0	—	—
2 000	—	—	2862,0	302,0	—	—
2 200	—	—	—	380,5	—	—
2 400	—	—	—	463,0	—	—
2 600	—	—	—	558,0	—	—
2 800	—	—	—	648,5	—	—
3 000	—	—	—	736,0	—	—
3 200	—	—	—	875,0	—	—
3 400	—	—	—	1025,5	—	—
3 600	—	—	—	1228,7	—	—

Table C.3 — Masses of flanges PN 10

DN	Masses in kilograms							
	Type 01	Type 02	Type 04	Type 05	Type 11	Type 12	Type 32	Type 34
200	9,5	9,0	8,0	16,5	11,5	10,5	3,0	5,0
250	12,0	11,5	10,0	24,0	15,5	13,0	3,5	6,5
300	13,5	13,0	11,5	31,0	18,0	15,0	4,0	8,0
350	20,5	19,5	15,0	39,5	24,5	23,5	7,5	12,0
400	27,5	26,5	21,0	49,5	29,5	29,0	9,0	15,0
450	33,5	32,5	26,0	63,0	34,0	33,5	10,5	16,5
500	40,0	39,0	31,0	75,5	39,5	40,5	12,5	20,0
600	54,5	52,5	43,5	124,0	56,0	56,0	14,5	24,0
700	—	—	—	182,5	65,0	—	—	—
800	—	—	—	260,0	87,0	—	—	—
900	—	—	—	344,0	106,0	—	—	—
1 000	—	—	—	473,5	123,0	—	—	—
1 200	—	—	—	765,0	184,0	—	—	—
1 400	—	—	—	—	252,0	—	—	—
1 600	—	—	—	—	363,0	—	—	—
1 800	—	—	—	—	445,5	—	—	—
2 000	—	—	—	—	558,0	—	—	—
2 200	—	—	—	—	702,5	—	—	—
2 400	—	—	—	—	860,5	—	—	—
2 600	—	—	—	—	1 010,5	—	—	—
2 800	—	—	—	—	1 208,0	—	—	—
3 000	—	—	—	—	1 461,0	—	—	—

Table C.4 — Masses of flanges PN 16

DN	Masses in kilograms							
	Type 01	Type 02	Type 04	Type 05	Type 11	Type 12	Type 32	Type 34
65	3,0	3,0	3,0	3,5	3,0	3,0	1,0	1,0
80	3,5	3,5	3,0	4,5	4,0	4,0	1,0	1,5
100	4,5	4,5	4,0	5,5	4,5	4,5	1,5	2,0
125	5,5	5,5	4,5	8,0	6,5	6,5	1,5	2,0
150	7,0	7,0	6,0	10,5	7,5	7,5	2,0	3,0
200	9,5	9,5	8,5	16,5	11,0	10,0	3,0	5,0
250	14,0	14,0	12,5	25,0	16,5	14,0	3,5	6,5
300	19,0	18,5	16,5	35,0	22,0	18,0	5,5	10,0
350	28,0	27,5	21,5	48,0	32,0	28,5	10,0	12,5
400	36,0	35,0	27,0	63,5	40,0	36,5	12,5	19,0
450	46,0	45,0	36,5	96,5	54,5	49,5	16,5	25,0
500	64,0	65,0	51,0	133,0	74,0	68,5	21,5	31,5
600	96,0	94,0	78,5	226,5	116,5	107,5	28,5	43,0
700	—	—	—	236,0	87,0	—	—	—
800	—	—	—	325,0	111,0	—	—	—
900	—	—	—	437,5	129,0	—	—	—
1 000	—	—	—	602,0	169,0	—	—	—
1 200	—	—	—	999,0	251,0	—	—	—
1 400	—	—	—	—	329,0	—	—	—
1 600	—	—	—	—	476,0	—	—	—
1 800	—	—	—	—	582,0	—	—	—
2 000	—	—	—	—	720,0	—	—	—

Table C.5 — Masses of flanges PN 25

DN	Masses in kilograms							
	Type 01	Type 02	Type 04	Type 05	Type 11	Type 12	Type 32	Type 34
200	14,5	14,0	11,5	22,5	17,0	15,0	4,5	7,5
250	20,0	19,5	17,0	33,5	24,0	21,0	5,5	10,0
300	26,5	26,0	22,0	46,5	31,5	28,0	8,5	14,5
350	42,0	41,0	32,0	68,0	48,0	46,5	14,5	22,0
400	55,0	54,0	42,5	89,5	63,0	59,5	18,0	28,5
450	64,5	63,0	50,0	120,0	75,5	71,5	21,0	32,5
500	84,0	82,0	63,5	150,0	96,5	89,5	27,0	43,5
600	127,5	124,5	98,5	244,5	138,6	129,5	34,0	56,5
700	—	—	—	—	143,5	—	—	—
800	—	—	—	—	193,5	—	—	—
900	—	—	—	—	237,0	—	—	—
1 000	—	—	—	—	310,5	—	—	—

Table C.6 — Masses of flanges PN 40

Masses in kilograms

DN	Type 01	Type 02	Type 04	Type 05	Type 11	Type 12	Type 32	Type 34
10	0,6	0,5	0,5	1,0	0,5	0,5	0,5	0,5
15	0,5	0,5	0,5	1,0	1,0	0,5	0,5	0,5
20	1,0	1,0	1,0	1,0	1,0	1,0	0,5	0,5
25	1,0	1,0	1,0	1,5	1,0	1,5	0,5	0,5
32	2,0	2,0	1,5	2,0	2,0	2,0	0,5	0,5
40	2,0	2,0	2,0	2,5	2,0	2,0	0,5	0,5
50	2,5	2,5	2,5	3,0	3,0	3,0	0,5	1,0
65	3,5	3,5	3,0	4,5	4,0	4,0	1,0	1,0
80	4,5	4,0	3,5	5,5	5,0	4,5	1,0	1,5
100	6,0	6,0	5,0	7,5	6,5	6,5	1,5	2,5
125	8,0	8,0	7,0	11,0	9,0	8,5	2,0	3,0
150	10,5	10,0	8,5	14,5	11,5	11,0	2,5	4,0
200	18,0	17,5	15,0	29,0	21,0	18,5	5,5	8,5
250	29,5	28,5	24,0	44,5	34,0	28,5	8,0	13,0
300	41,5	40,5	33,5	64,0	47,5	41,5	12,75	20,54
350	62,0	60,74	47,0	89,5	69,0	60,0	19,31	29,50
400	89,5	88,0	69,5	127,0	98,0	83,5	30,38	46,11
450	91,5	90,0	72,5	154,0	105,08	87,5	28,40	48,55
500	120,5	118,0	92,0	188,0	130,5	107,5	35,31	61,70
600	189,5	186,0	149,5	331,0	211,5	176,0	53,32	91,74

Table C.7 — Masses of flanges PN 63

Masses in kilograms

DN	Type 01	Type 05	Type 11	Type 12
50	4,5	5,0	4,5	4,5
65	5,0	6,0	5,5	5,5
80	6,5	7,5	6,5	6,5
100	8,5	10,5	9,5	9,0
125	12,5	16,5	14,5	14,0
150	18,0	24,5	21,5	20,0
200	30,5	40,5	34,0	—
250	43,0	58,0	48,0	—
300	58,5	83,5	67,5	—
350	91,5	116,0	97,5	—
400	121,0	155,5	129,0	—

Table C.8 — Masses of flanges PN 100

Masses in kilograms

DN	Type 01	Type 05	Type 11	Type 12
10	1,0	1,0	1,0	1,0
15	1,0	1,5	1,0	1,0
20	2,0	2,0	2,0	2,0
25	2,5	2,5	2,5	2,5
32	3,0	3,5	3,0	3,0
40	4,0	4,5	4,0	4,0
50	5,5	6,0	6,0	5,5
65	7,0	8,0	7,5	7,0
80	8,0	9,5	9,0	8,0
100	11,0	14,0	13,0	12,0
125	18,5	22,5	21,0	18,5
150	25,0	30,5	28,0	24,5
200	44,5	54,5	50,0	—
250	71,0	87,5	81,0	—
300	107,0	131,5	117,97	—
350	154,0	179,0	167,25	—
400	199,5	—	—	—
500	339,5	—	—	—

Annex D
(informative)

Additional materials

Additional materials may be used as follows:

Table D.3 — Additional materials

Material name	Material number	Material group
C21 ^a	1.0432	1EO
C22.8 ^a	1.0460	3EO
^a According to DIN 2528		

Annex E
(informative)

Determination of p/T ratings for flanges using EN materials

The p/T ratings in Tables 15 to 18 were calculated in accordance with the following rules:

- a) the ratings are calculated on the basis of strength values specified in European material standards;
- b) the pressure is calculated from $PS = PN \left(\frac{R_e}{225} \right)$;

it is limited to $PS \leq PN$;
- c) for the value R_e the value R_{eH} or $R_{p0,2}$ and the rupture stress $\sigma_{r/100\ 000}$ is used for all materials. For austenitic materials, the value $R_{p1,0}$ (1 % proof stress) is used for the additional p/T rating tables;
- d) to take a product thickness of 40 mm as basis for the calculation (medium flange face thickness);
- e) if strength values are not specified for specific temperatures, the p/T ratings shall also not be calculated;
- f) if a material group comprises various materials, the material with the lowest strength shall be chosen for calculation. If this is a casting and if its strength values are only slightly below the strength values of a forging or flat product, the strength values of the forging or flat product have been chosen.

NOTE The rules in this annex are given for information only.

Annex F
(informative)

Determination of p/T ratings for flanges using ASTM materials

The p/T ratings in Tables 19 and 20 were calculated in accordance with the following rules:

- a) the ratings are calculated based on strength values specified in the ASME Boiler and Pressure Vessel Code — Section II: Materials — Part D – Properties, 1995 edition July, 1995 – 1996 addenda issued 31st December 1996;
- b) the pressure is calculated from: $PS = PN \left(\frac{\text{design strength}}{25} \right)$;
- c) design strengths are determined from:
 - yield strengths at temperatures below the creep range;
 - $1,5 \times$ maximum allowable stress at temperature for temperatures in the creep range;
 - a maximum of 225 N/mm^2 .

NOTE Temperatures in the creep range are defined as:

- above $371 \text{ }^\circ\text{C}$ ($700 \text{ }^\circ\text{F}$) for material groups 1C1 to 1C7;
- above $454 \text{ }^\circ\text{C}$ ($850 \text{ }^\circ\text{F}$) for material groups 1C9 to 1C14;
- above $510 \text{ }^\circ\text{C}$ ($950 \text{ }^\circ\text{F}$) for material groups 2C1 to 2C7.

Table F.1 gives the design strengths used to calculate *PS*.

Table F.1 — Design strength for PN flanges in ASTM materials

Material group	Maximum allowable temperature <i>TS</i> in °C																				
	RT ^a	50	100	150	200	250	300	350	375	400	425	450	475	500	510	520	530	540	550	575	600
Design strength N/mm ²																					
1C1	225,0	225,0	225,0	219,8	213,0	202,7	188,2	179,6	175,0	151,9	125,8	87,6	59,2	38,4	—	—	—	—	—	—	—
1C2	225,0	225,0	225,0	225,0	225,0	225,0	209,5	200,1	192,2	151,9	125,8	87,6	59,2	38,4	—	—	—	—	—	—	—
1C3	225,0	225,0	219,2	213,6	207,4	197,2	183,2	174,8	169,5	142,7	119,4	86,6	59,2	38,4	—	—	—	—	—	—	—
1C4	206,8	202,9	188,3	183,3	177,7	169,3	157,1	150,3	148,1	133,5	113,1	85,6	59,2	38,4	—	—	—	—	—	—	—
1C5	225,0	225,0	225,0	217,7	210,3	205,1	199,1	192,9	187,1	167,4	163,7	159,1	146,0	105,3	—	—	—	—	—	—	—
1C7	225,0	225,0	225,0	225,0	225,0	225,0	218,6	211,4	204,4	181,0	181,0	177,5	160,8	116,7	95,1	82,8	70,5	59,9	55,1	—	—
1C9	225,0	225,0	225,0	225,0	225,0	225,0	218,6	211,4	207,6	203,9	198,9	193,9	154,3	112,2	96,1	85,0	73,8	63,4	55,6	38,5	26,4
1C10	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	223,2	219,5	215,2	164,4	125,7	113,8	101,1	88,4	76,5	67,2	46,0	30,1
1C13	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	224,0	219,0	212,8	204,8	135,5	93,1	82,7	74,5	66,3	58,6	52,7	38,8	27,2
1C14	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	225,0	196,8	133,1	113,8	100,4	86,9	74,5	65,6	45,7	31,4
2C1	206,8	199,3	170,3	154,9	143,7	135,4	127,8	123,1	121,6	119,1	116,0	114,1	112,2	110,4	109,6	108,9	108,1	106,8	103,5	91,2	73,8
2C2	206,8	200,5	175,8	160,4	148,6	139,1	131,7	126,9	124,5	122,7	121,4	120,2	119,5	118,4	117,9	117,5	117,2	116,8	116,4	107,7	87,1
2C3	172,4	166,5	143,7	130,1	119,5	111,2	105,2	100,2	98,3	96,4	94,5	92,7	—	—	—	—	—	—	—	—	—
2C4	206,8	202,1	183,7	170,7	159,6	150,1	142,3	136,4	133,5	131,6	129,7	128,5	127,2	126,0	125,5	125,0	124,5	123,9	122,7	111,9	88,6
2C5	206,8	203,0	188,0	176,3	165,7	156,9	149,7	144,1	141,9	141,3	140,0	139,4	138,8	138,6	138,6	138,3	138,1	136,9	132,3	114,6	86,6
2C6	193,1	188,8	172,5	163,2	153,9	146,3	139,3	133,1	130,6	128,1	125,0	122,5	120,0	117,5	116,5	111,4	106,3	101,2	96,0	80,8	63,5
2C7	193,1	189,0	173,1	163,2	154,5	147,0	140,0	133,6	130,7	128,8	125,7	123,2	120,7	118,2	117,2	113,4	109,5	106,1	104,2	93,6	73,3
^a -10 °C to 50 °C.																					

Annex ZA
(informative)

Essential safety requirements

Clauses of this European Standard addressing essential requirements or other provisions of EU Directives

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association (EFTA) and supports essential requirements of EU Directive 97/23/EC (Pressure Equipment Directive, PED).

WARNING Other requirements and other EU Directives **may** be applicable to the products falling within the scope of this standard.

The following clauses of this standard are likely to support requirements of Directive 97/23/EC.

Compliance with the clauses of this standard provides one means of conforming with the specific essential requirements of the Directive concerned and associated EFTA regulations.

Table ZA.1 — Correspondence between this European Standard and Directive 97/23/EC

Clause/ subclause of this European Standard	Essential requirements (ERs) of Directive 97/23/EC		Qualifying remarks/ notes
5.1	Annex 1, Clause 4	Materials: Materials for pressure equipment to be suitable during lifetime — unless replacement is foreseen.	—
	Annex 1, Clause 4.1a)	Materials for pressurized parts to have appropriate properties for all operating and test conditions: — to be sufficiently ductile and tough; — characteristics of material to comply with ERs at 7.5 — to be selected in order to prevent brittle-type fracture, or appropriate measures to be taken.	—

Table ZA.1 (continued)

Clause/ subclause of this European Standard	Essential requirements (ERs) of Directive 97/23/EC		Qualifying remarks/ notes
5.5	Annex 1, Clause 2	Design	—
	Annex 1, Clause 2.1	To be designed to ensure safety throughout intended life — to incorporate appropriate safety coefficients.	—
	Annex 1, Clause 2.2	To be designed for adequate strength.	—
	Annex 1, Clause 2.2.1	To be designed for loadings appropriate to its intended use.	
	Annex 1, Clause 2.2.2	To be designed for appropriate strength based on a calculation method.	—
	Annex 1, Clause 2.2.3a)	Requirements to be met by applying one of the following methods — design by formula.	—
	Annex 1, Clause 2.2.3b)	Design calculations to establish the resistance of equipment, in particular: — account to be taken of combinations of temperature and pressure; — maximum stresses and peak stresses to be within safe limits.	—
	Annex 1, Clause 7	Specific quantitative requirements for certain pressure equipment.	—
	Annex 1, Clause 7.1.2	Permissible general membrane stresses, for predominantly static loads and for temperatures outside the creep range not exceeding the smaller of the following values, according to the material used. Ferritic steels excluding fine grain steel and specially heat treated steel: — $2/3 Re/t$ and $5/12 Rm/20$. Austenitic steels: — if elongation after rupture exceeds 30 %: $2/3 Re/t$; — if elongation after rupture exceeds 35 %: $5/6 Re/t$ and $1/3 Rm/t$.	—
5.10	Annex 1, Clause 3.1.5	Traceability: Materials making up component parts to be identified by suitable means from receipt, through production, up to final test.	—

EN 1092-1:2001 (E)

Bibliography

EN 287-1, *Approval testing of welders for fusion welding — Part 1: Steels.*

EN 288-1, *Specification and qualification of welding procedures for metallic materials — Part 1: General rules for fusion welding.*

EN 1514-1, *Flanges and their joints — Dimensions of gaskets for PN-designated flanges — Part 1: Non-metallic flat gaskets with or without inserts.*

EN 1514-2, *Flanges and their joints — Dimensions of gaskets for PN-designated flanges — Part 2: Spiral wound gaskets for use with steel flanges.*

EN 1514-3, *Flanges and their joints — Dimensions of gaskets for PN-designated flanges — Part 3: Non-metallic PTFE envelope gaskets.*

EN 1514-4, *Flanges and their joints — Dimensions of gaskets for PN-designated flanges — Part 4: Corrugated, flat or grooved metallic and filled metallic gaskets for use with steel flanges.*

EN 1515-1, *Flanges and their joints — Bolting — Part 1: Selection of bolting.*

EN 1515-2:1994, *Flanges and their joints — Bolting — Part 2: Combination of flange materials and bolting materials for steel flanges — PN designated.*

EN 10204, *Metallic products — Type of inspection documents (includes Amendment A1:1995).*

EN ISO 4287, *Geometrical product specification (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters (ISO 4287:1997).*

ISO 4200, *Plain end steel tubes, welded and seamless; General tables dimensions and masses per unit length.*

DIN 2528, *Flanges — Steel flanges ready for use — Materials.*

AD Merkblatt W10: 1987, *Materials for low temperature application — Ferritic materials.*

AD Merkblatt W1: 1995, *Hot rolled products in unalloyed and alloyed steels.*

ASME, *Boiler and Pressure Vessel Code — Section II: Materials — Part D — Properties 1995 edition July, 1995 - 1996 addenda issued 31 December 1996.*

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.

BSI
389 Chiswick High Road
London
W4 4AL